





OPAL Reflector Vessel & leak mitigation

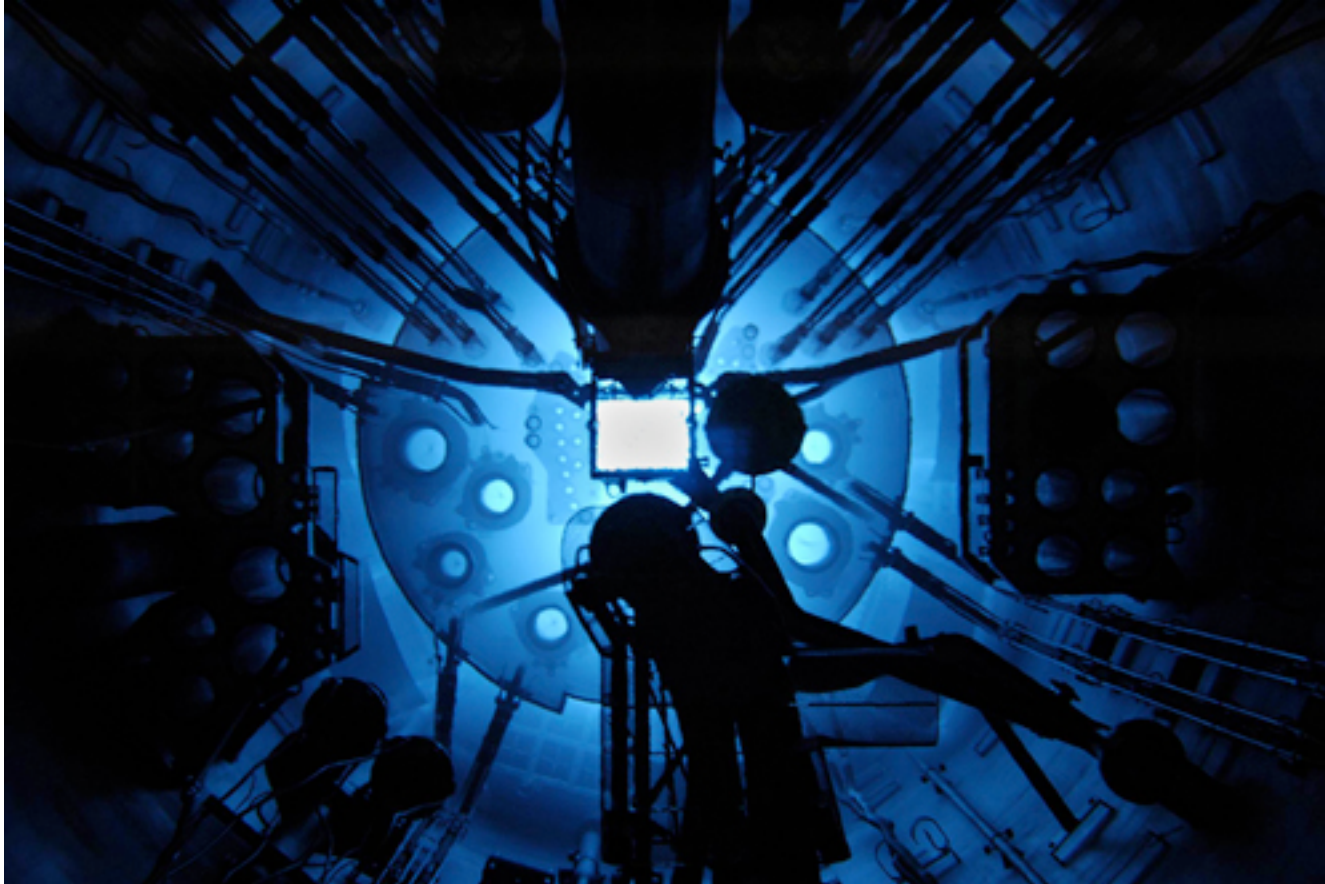


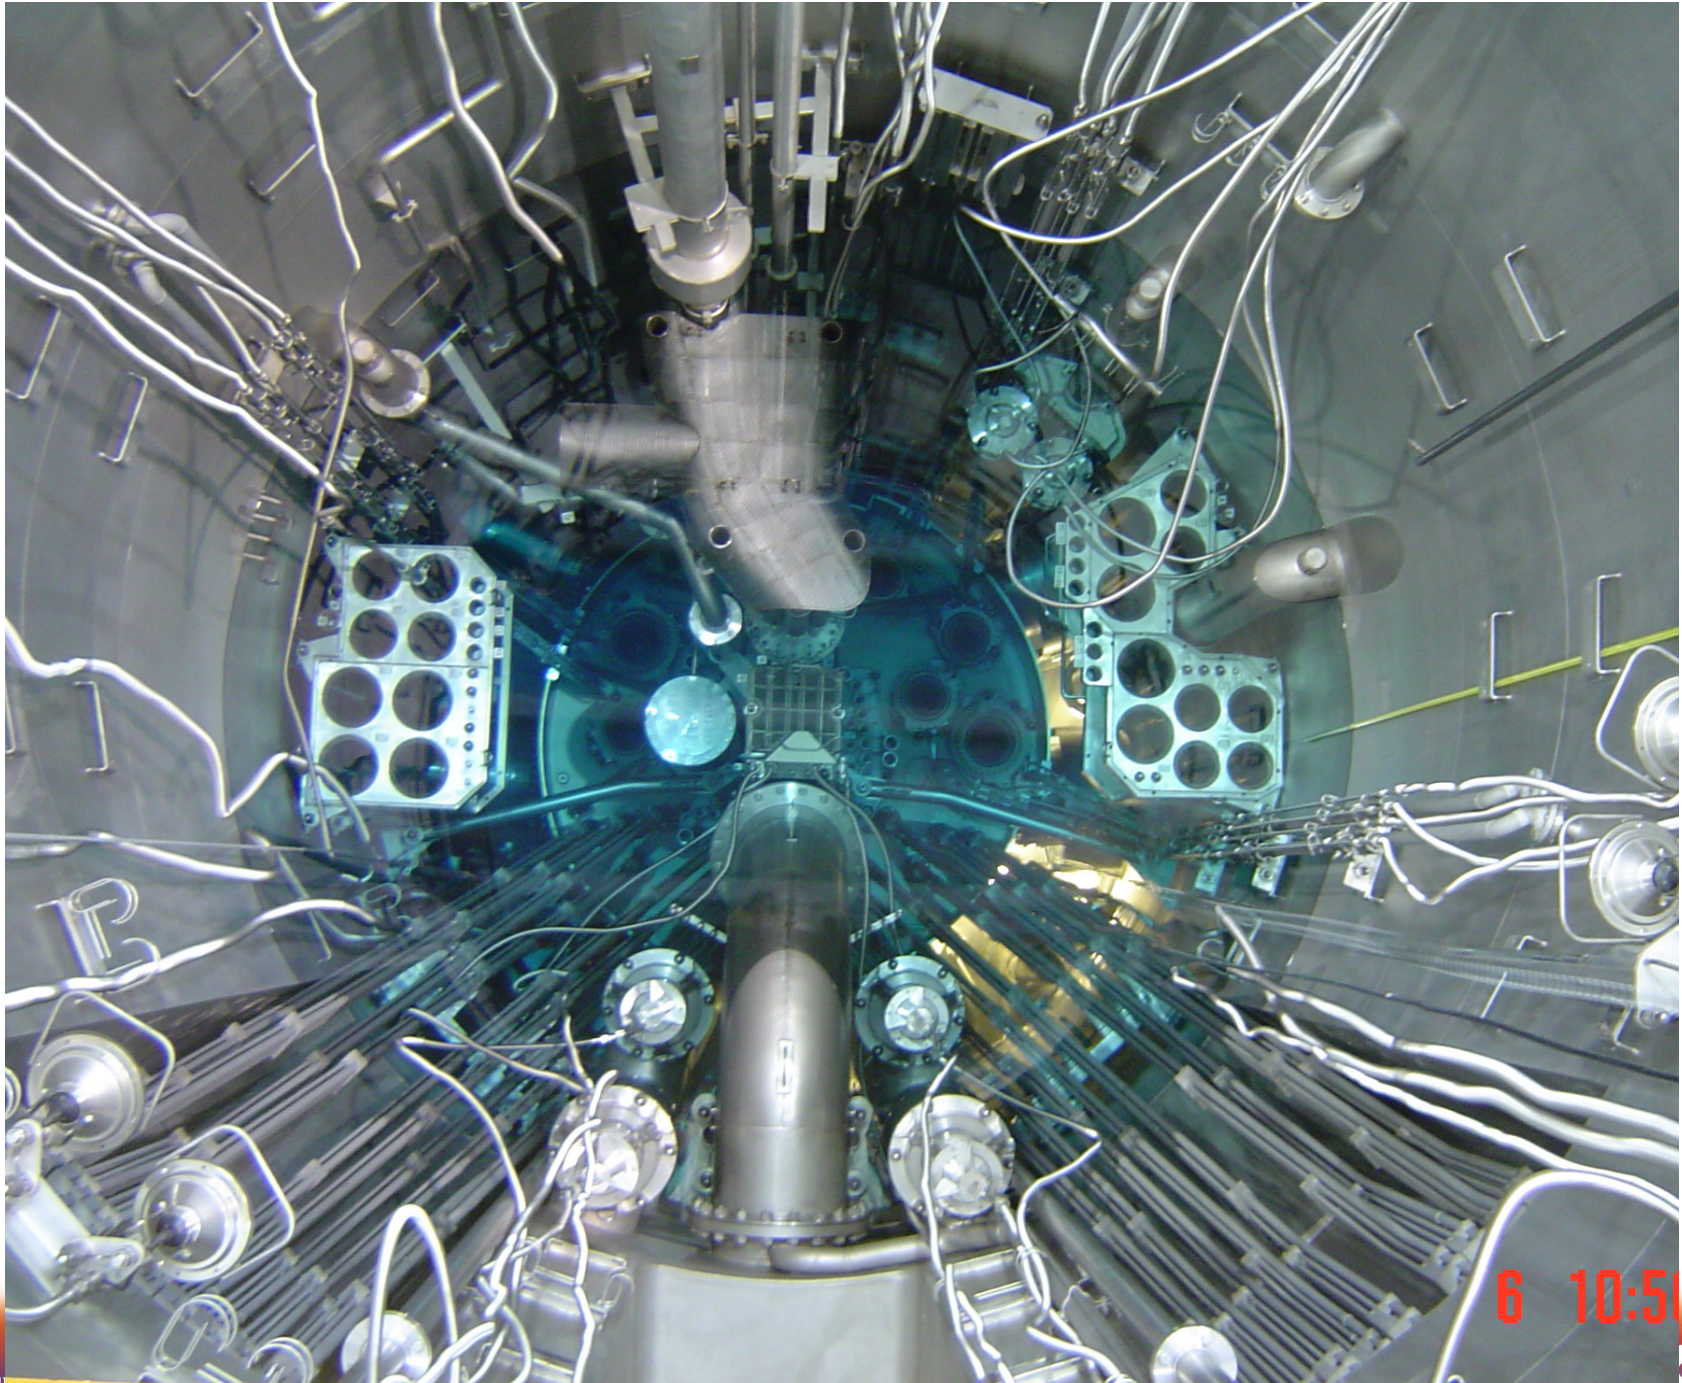


6 10:51

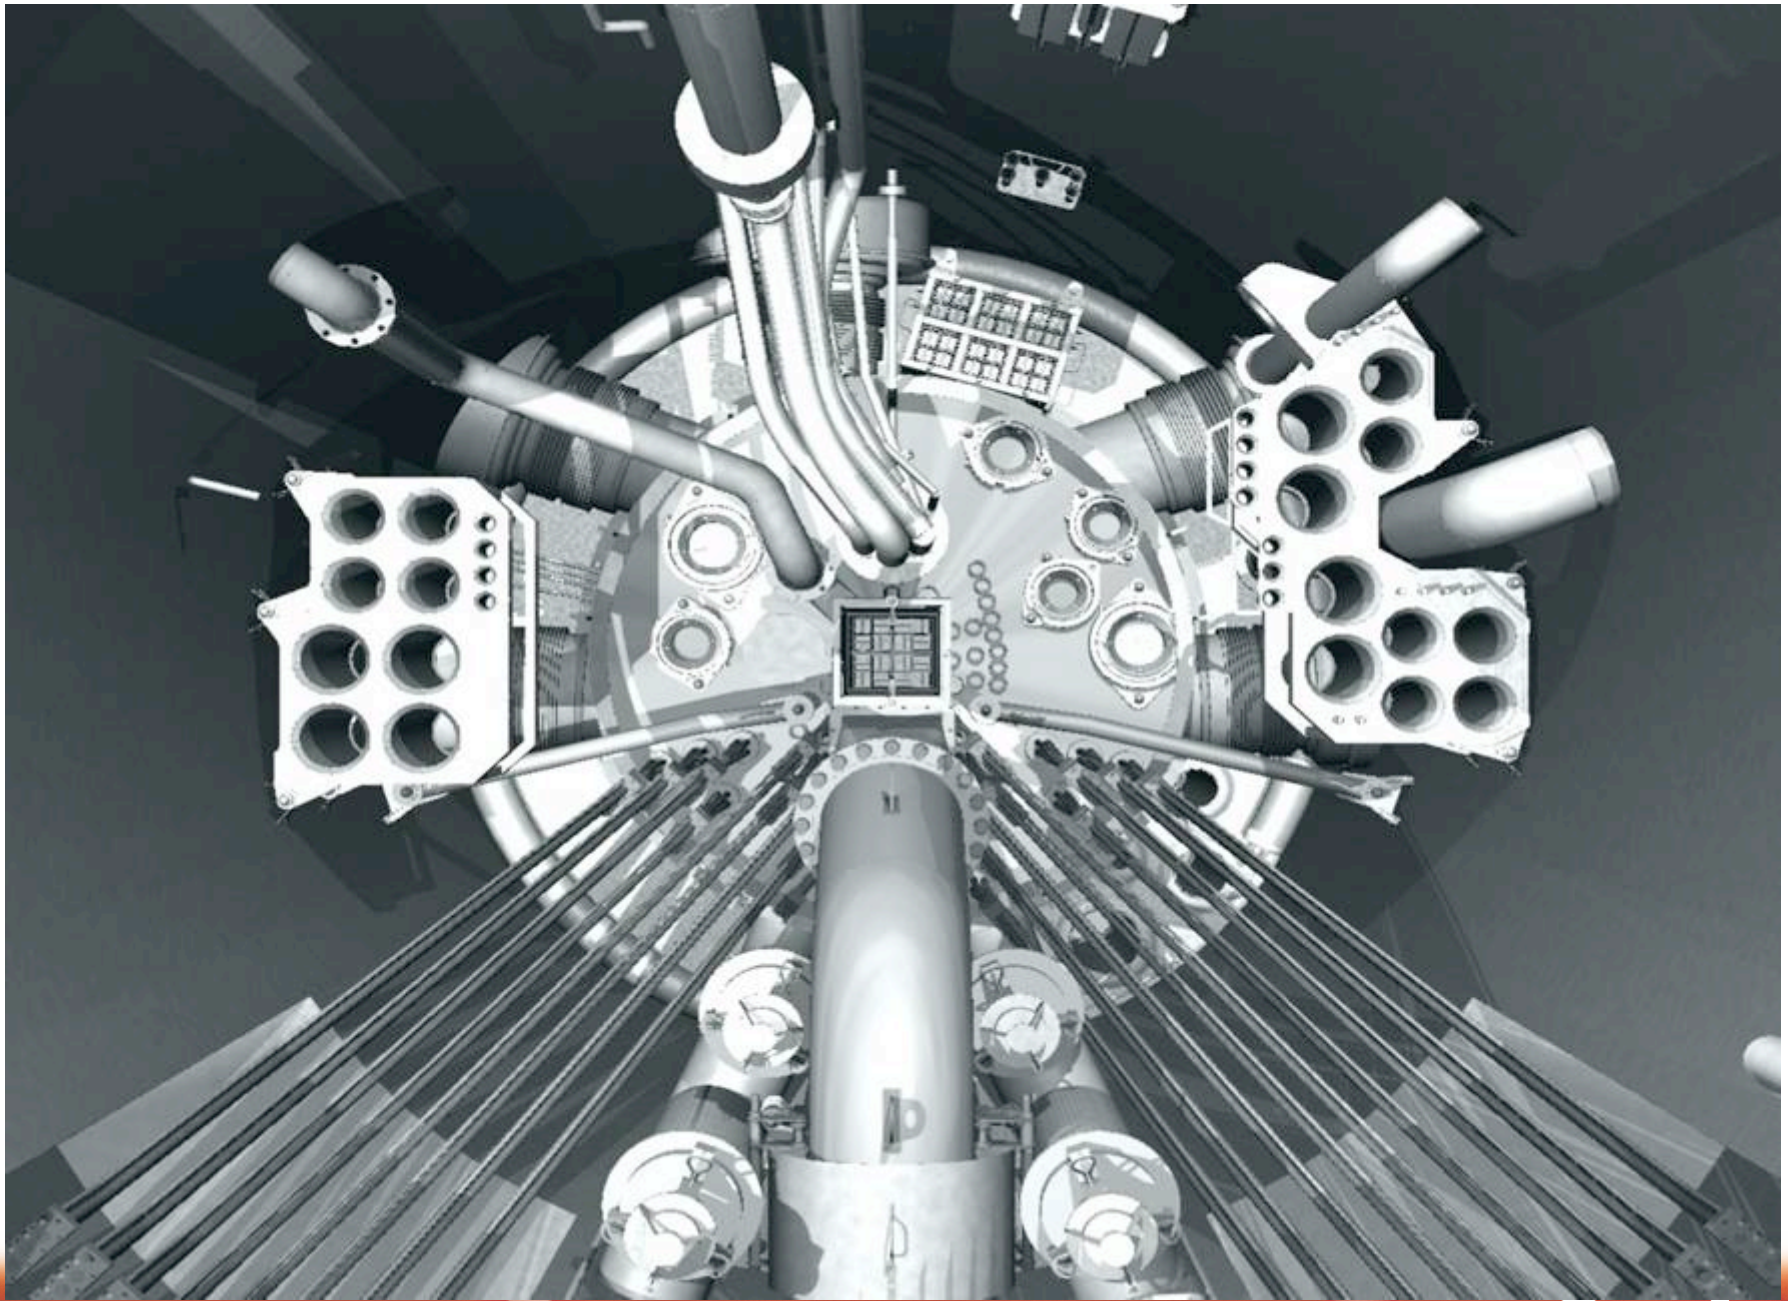

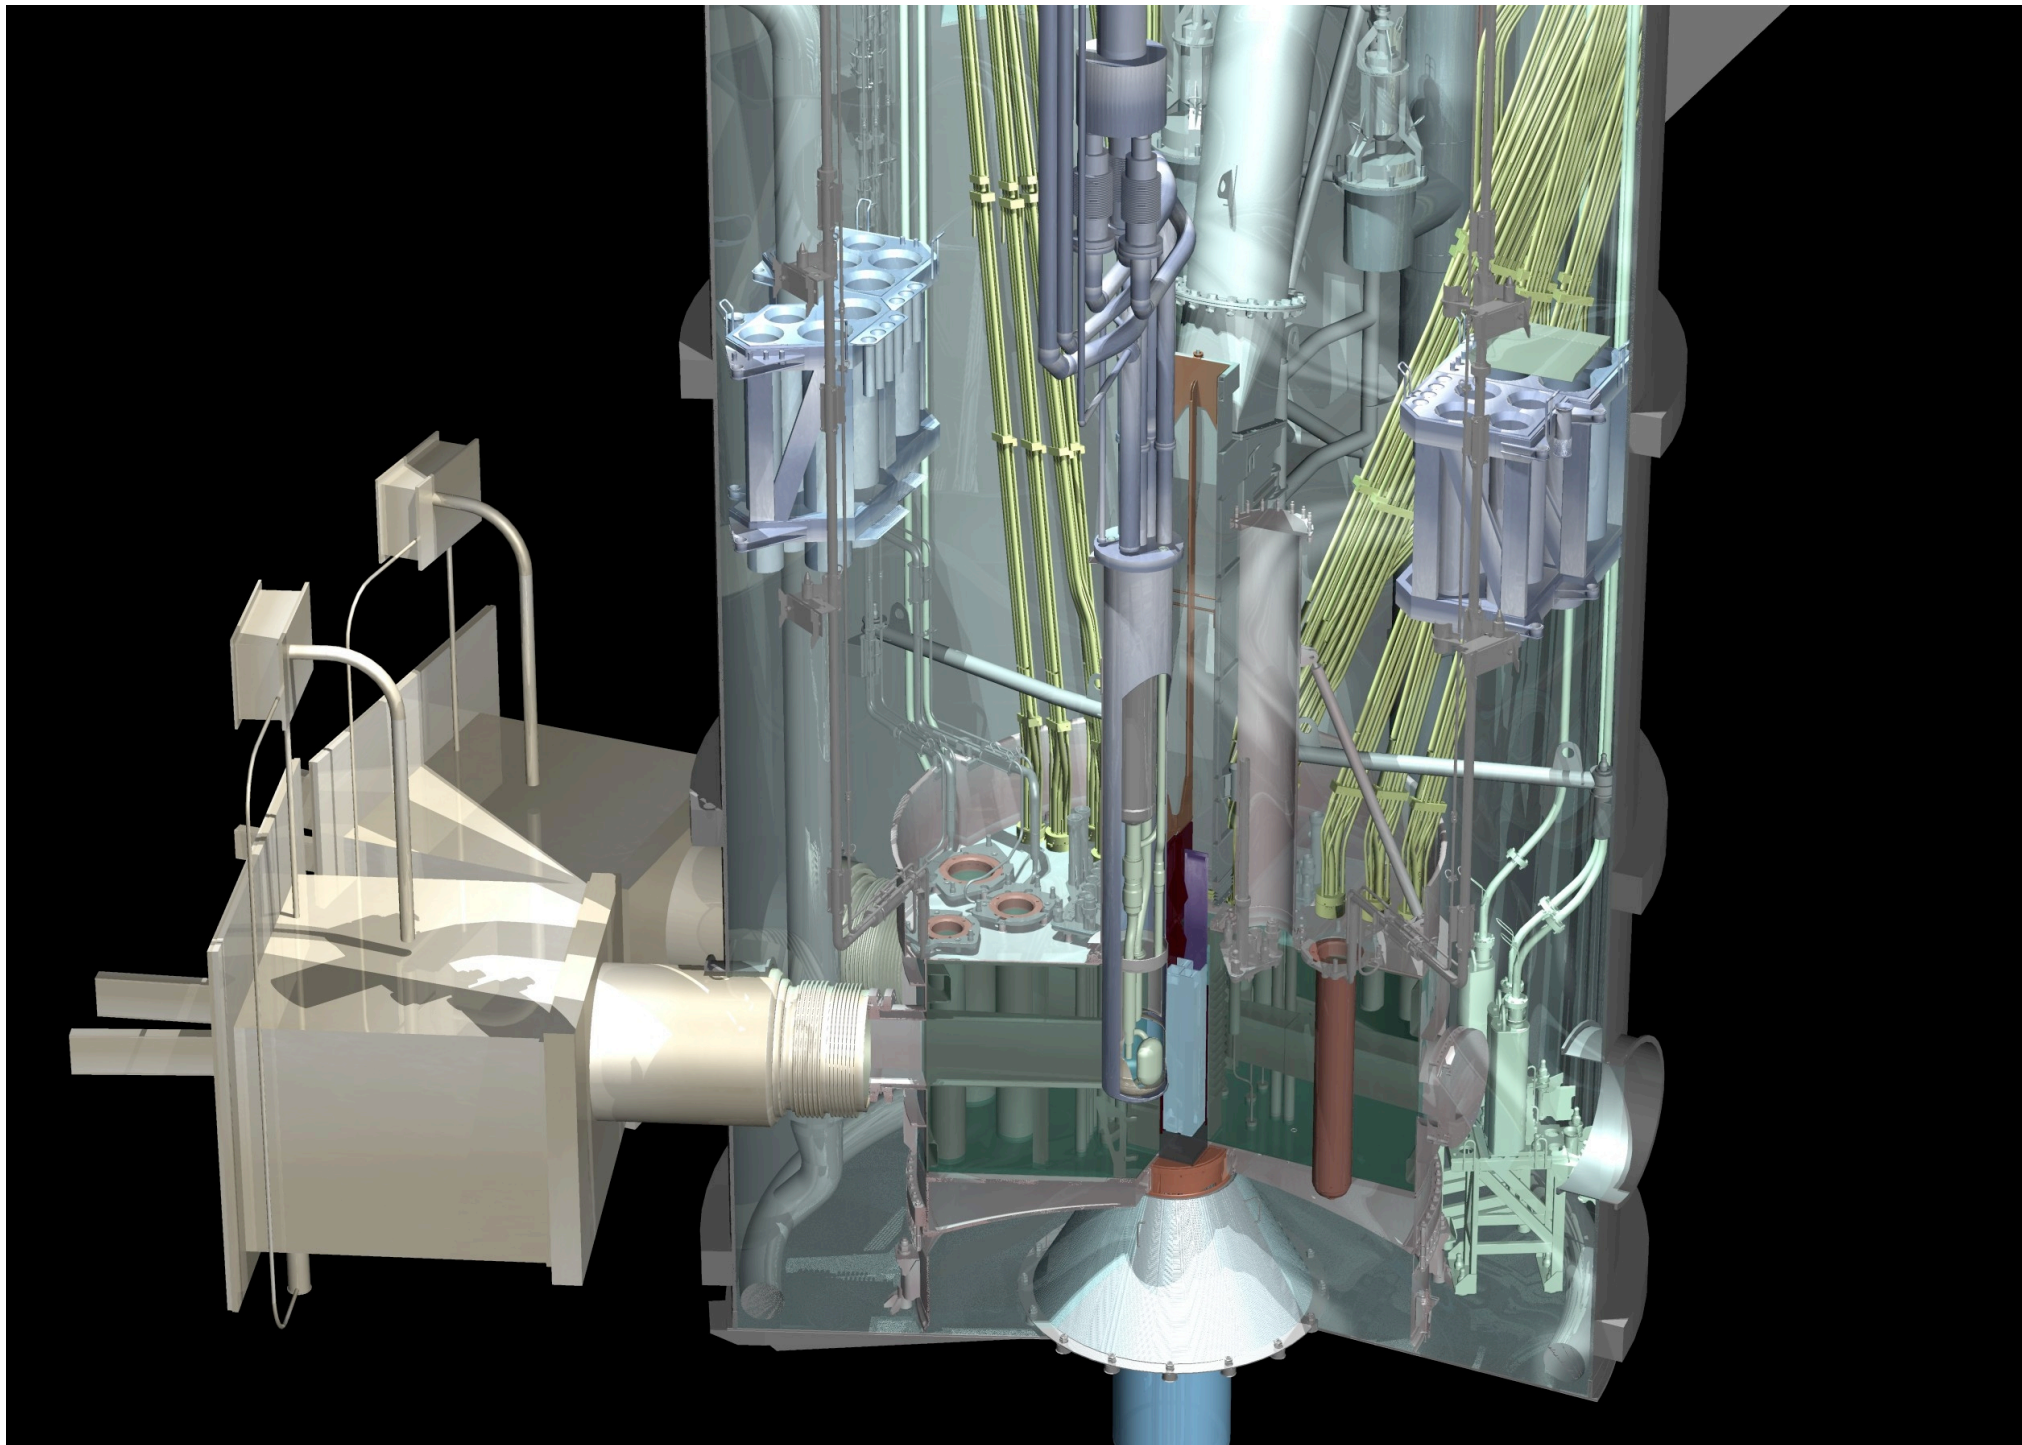


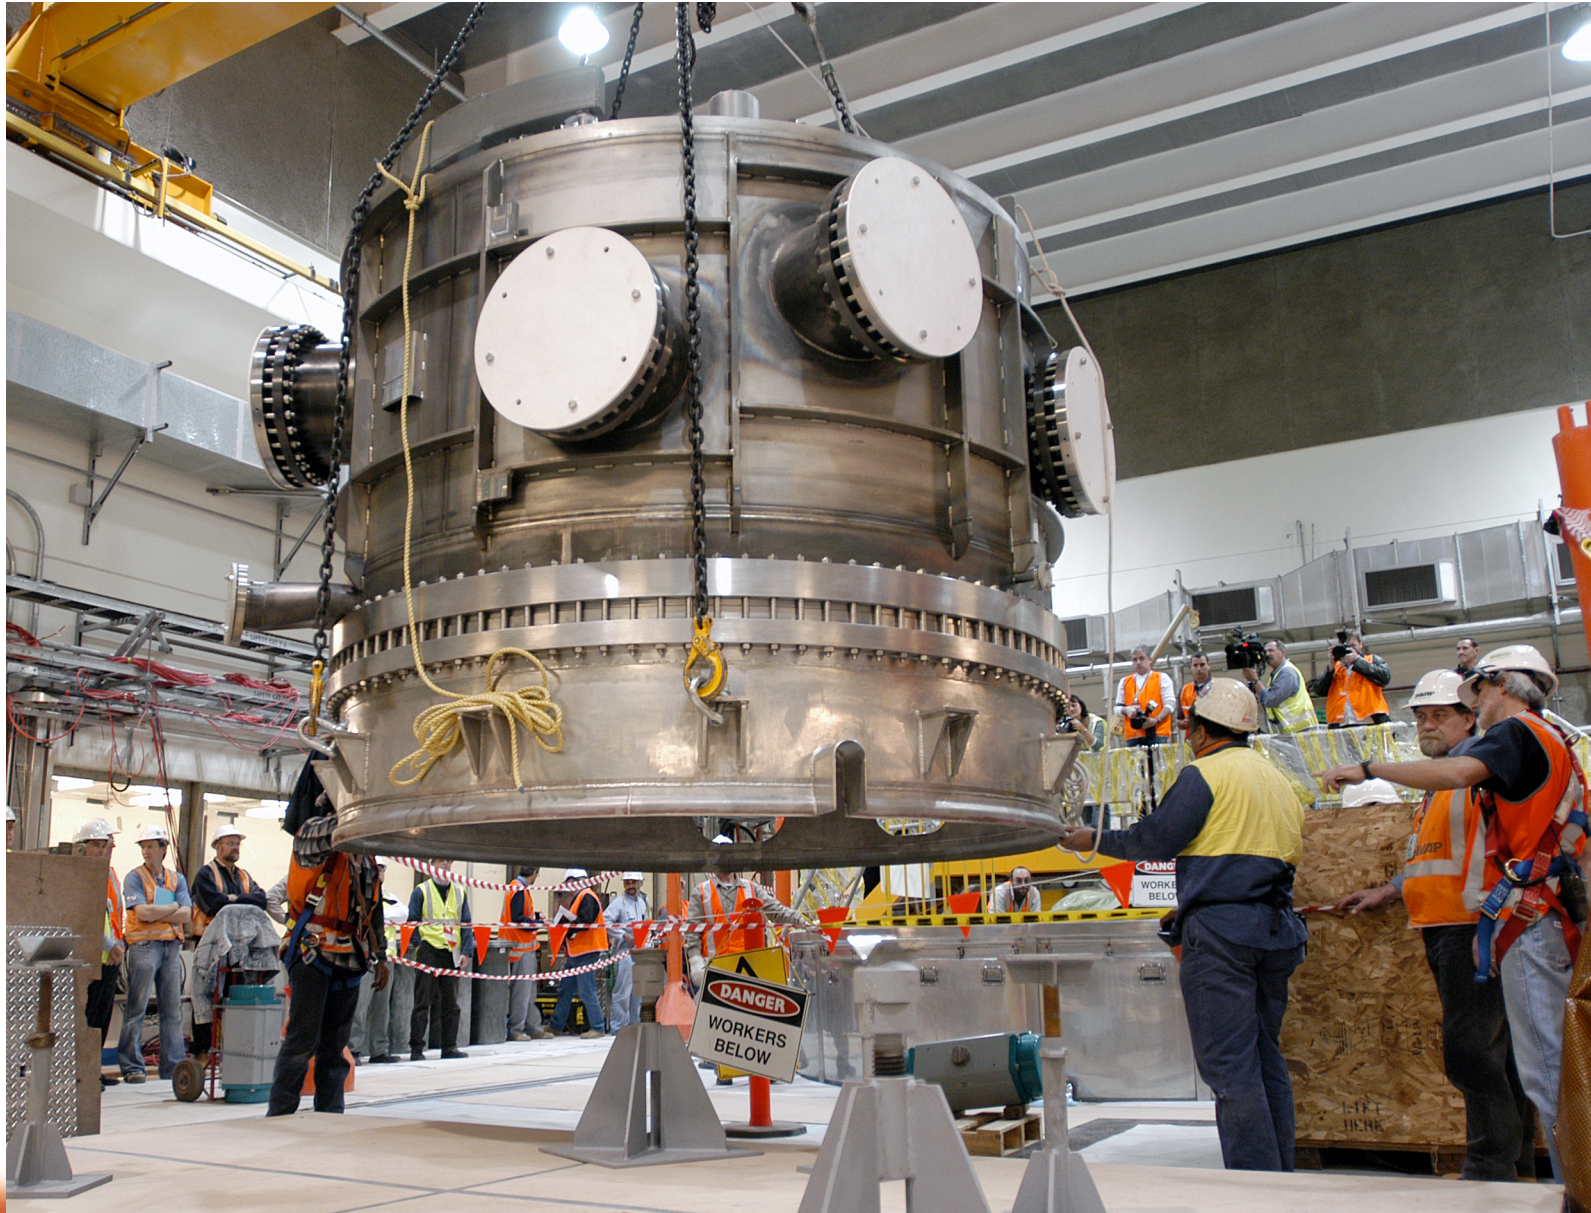



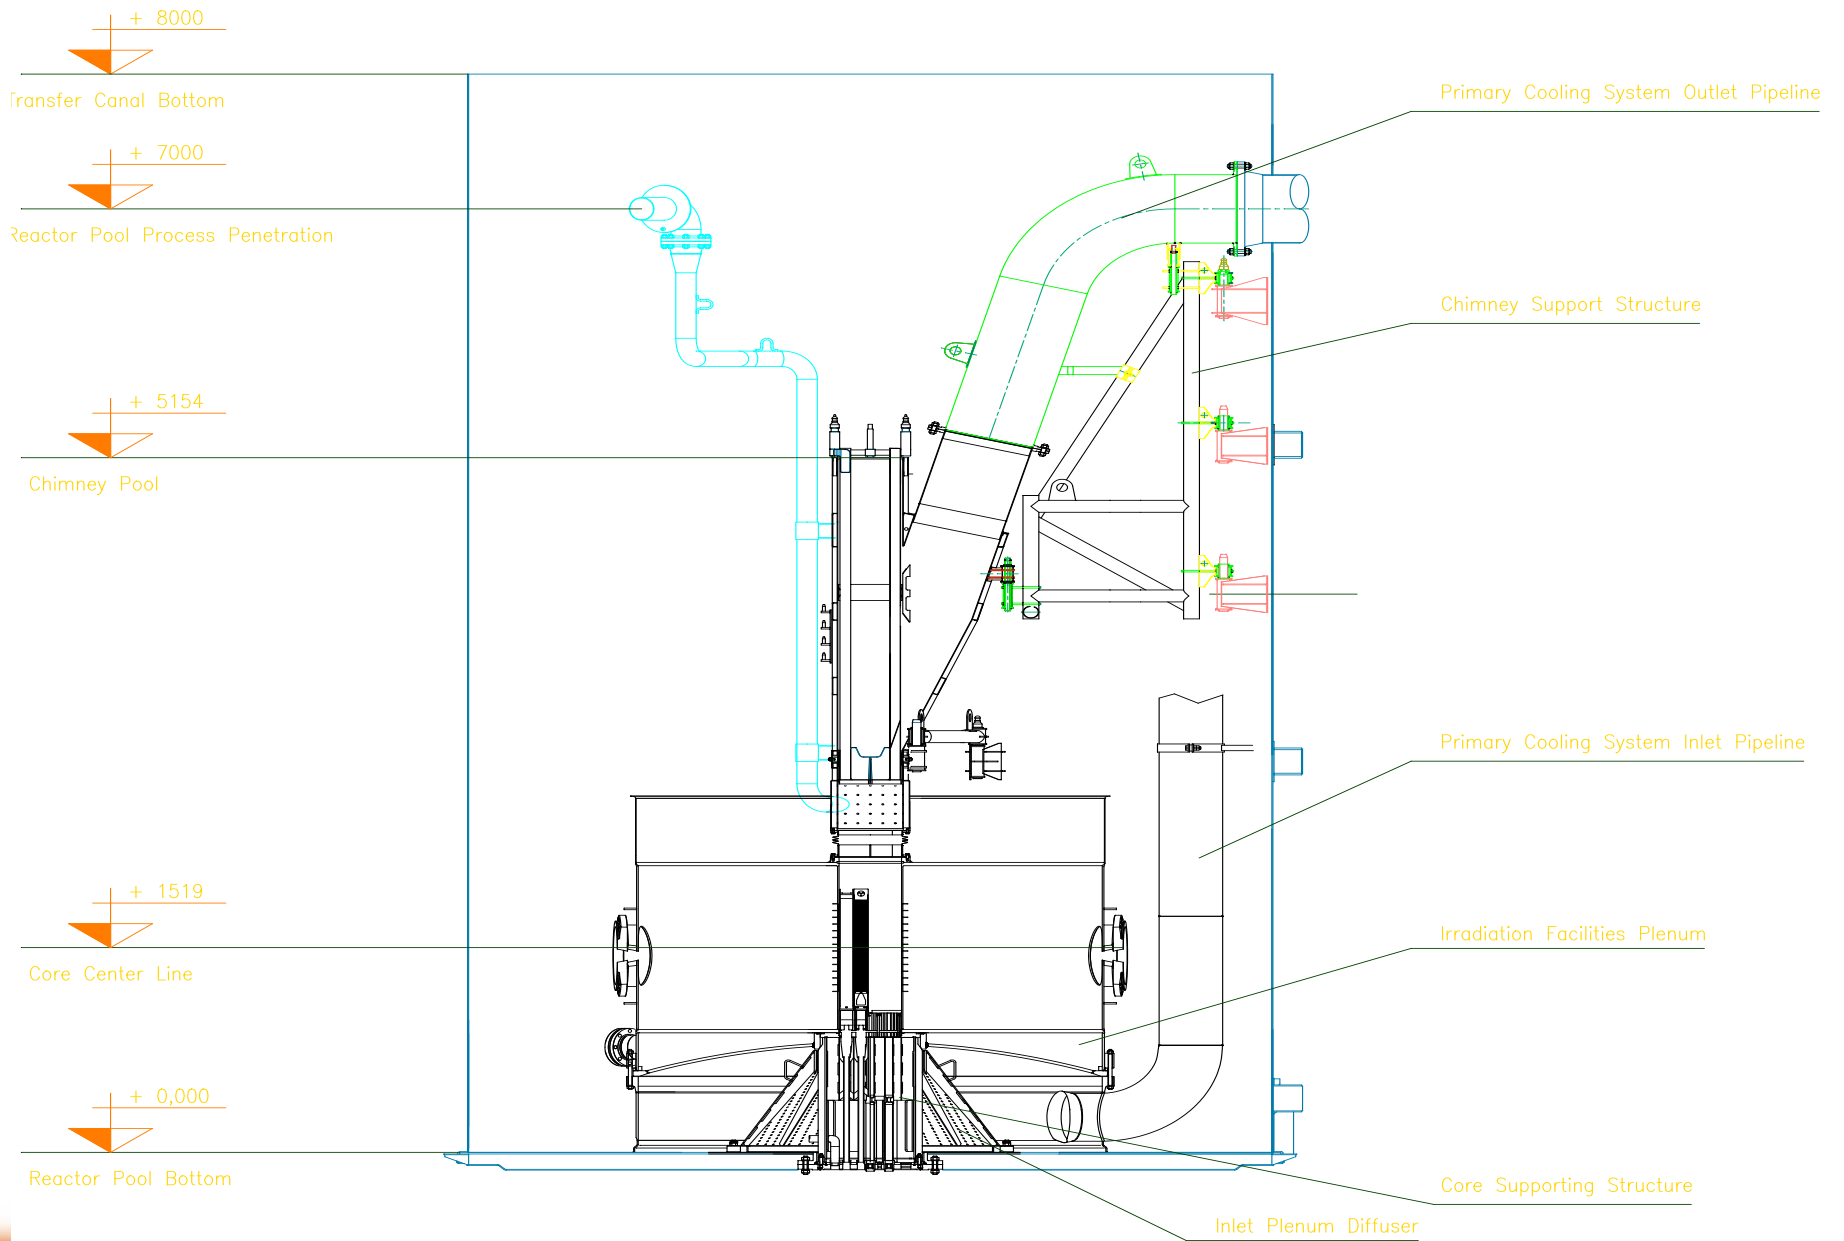

Timeline of Events

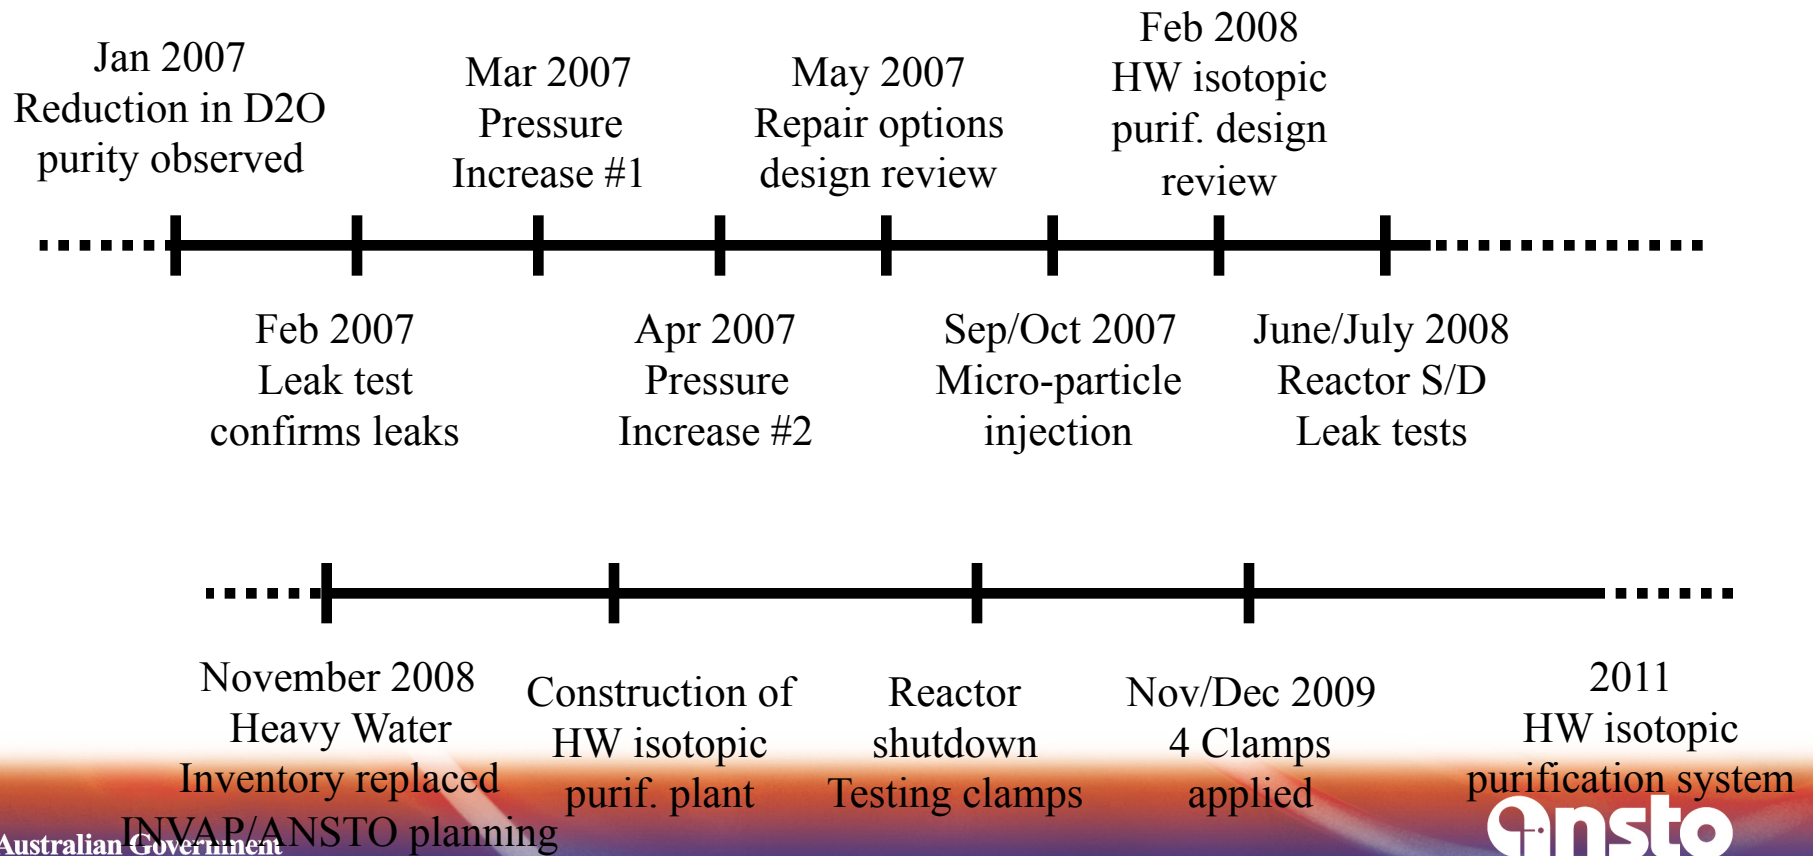

RVE He Leak Test - Method


- Reactor Pool drained to 7m (normal level 12.6m)
- RVE completely drained of heavy water
- Helium gas injected into RVE to a maximum pressure of 97kPa providing a DP of 40kPa (max. DP was limited by pressure rating constraints of CNS equipment)
- All RVE flanges and penetrations carefully checked for leakage, particularly the neutron beam flanges

RVE He Leak Test - Results



- First helium bubbles were observed 3 hours into the test from the TNG1-3 flange
- Smaller helium bubbles were observed on day 4 from CNG1-3 and TNG4
- No other leakages observed
- Collection of bubbles from the TNG1-3 leaks showed a leak rate consistent with the isotopic purity degradation

**1 small leak
(~2.5%)**

**6 Leaks comprising
~95% of leakage**

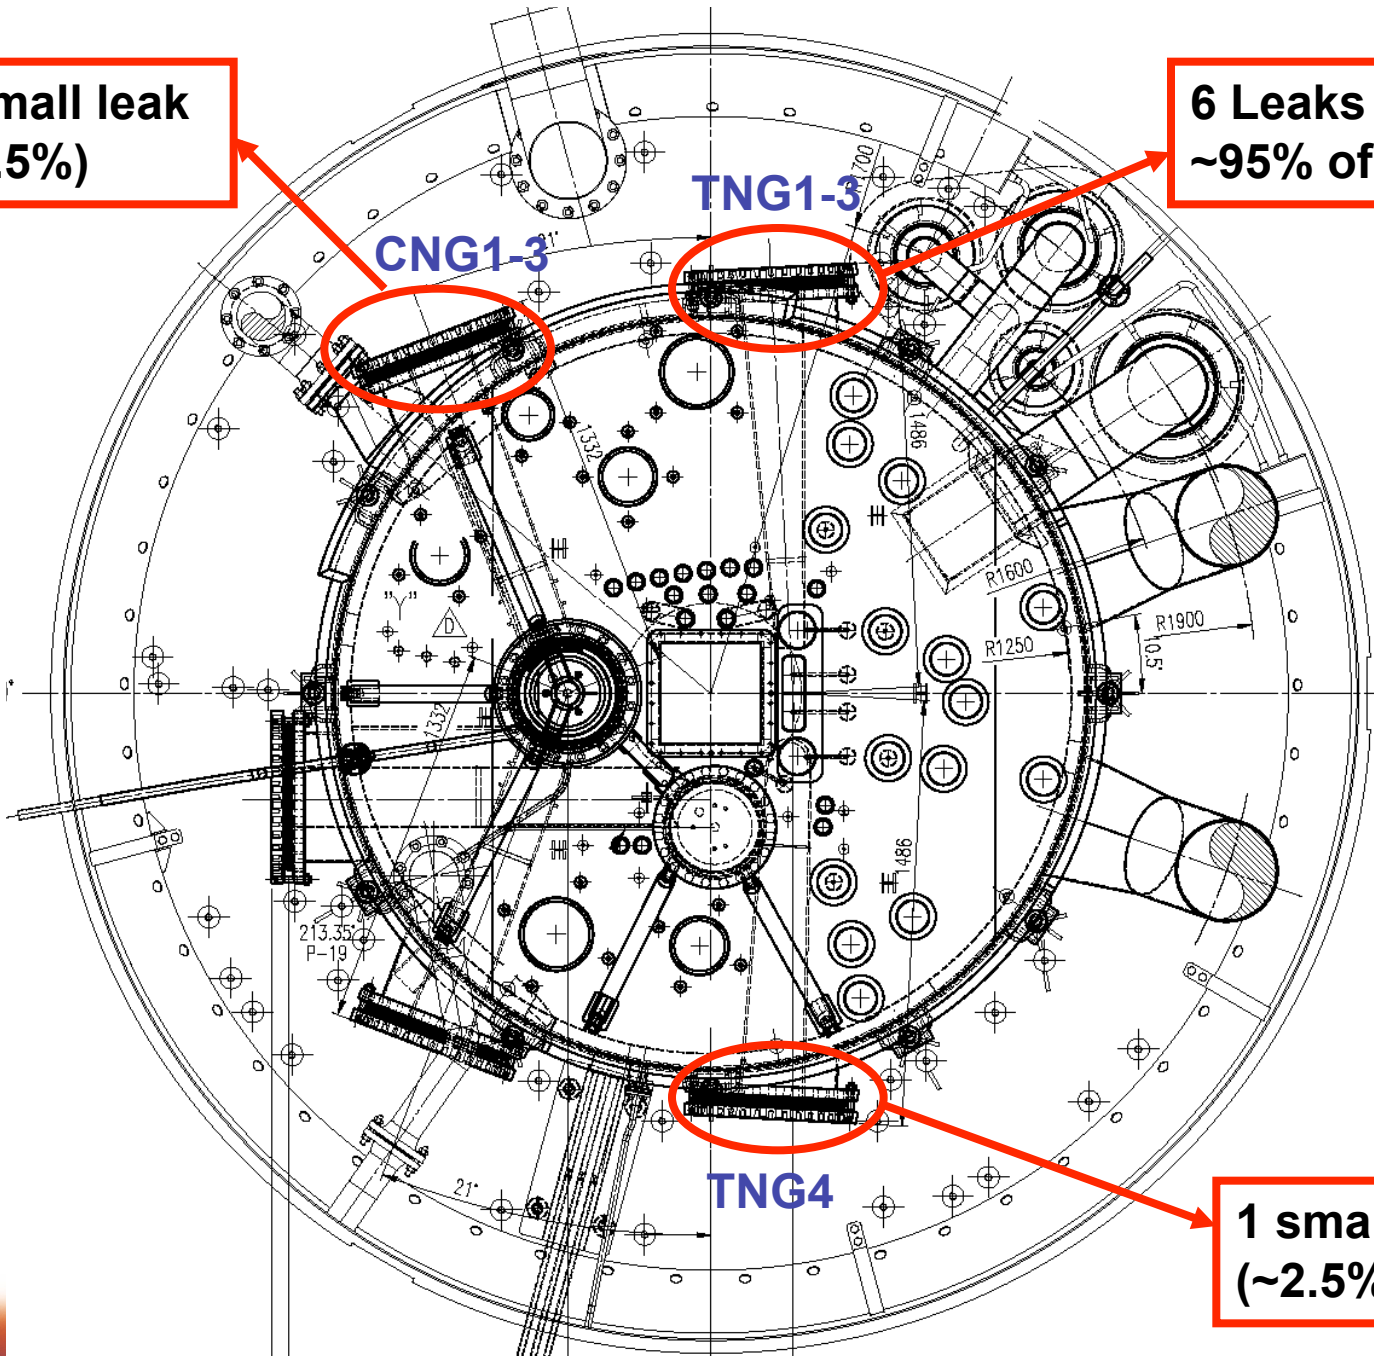


**1 small leak
(~2.5%)**

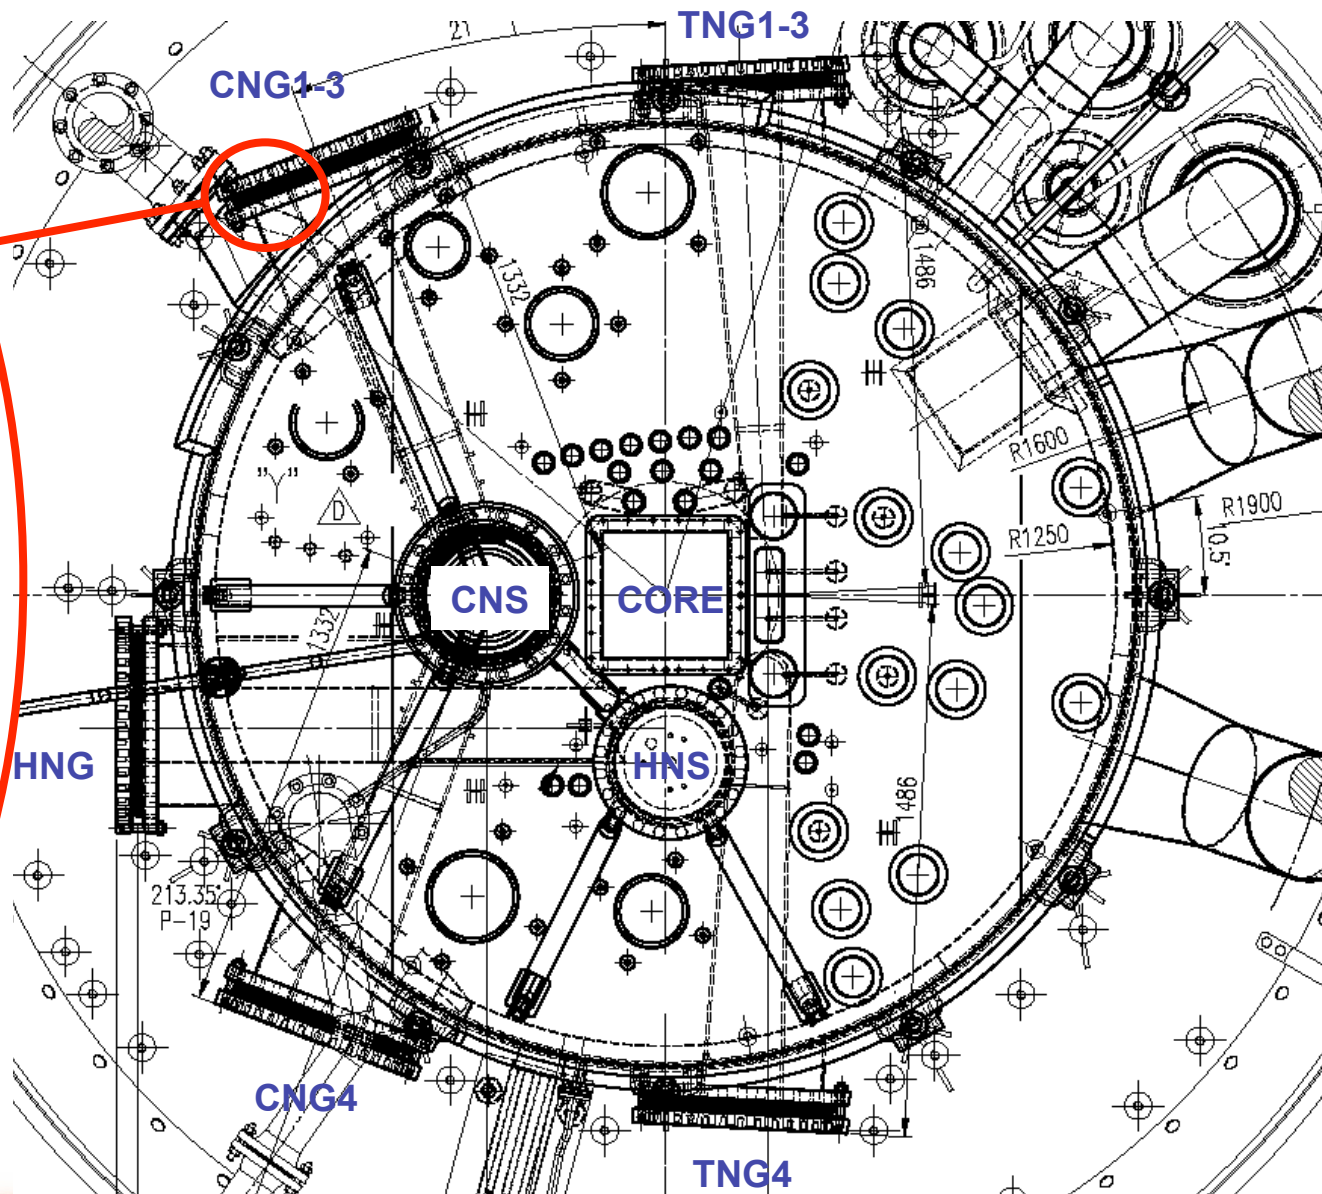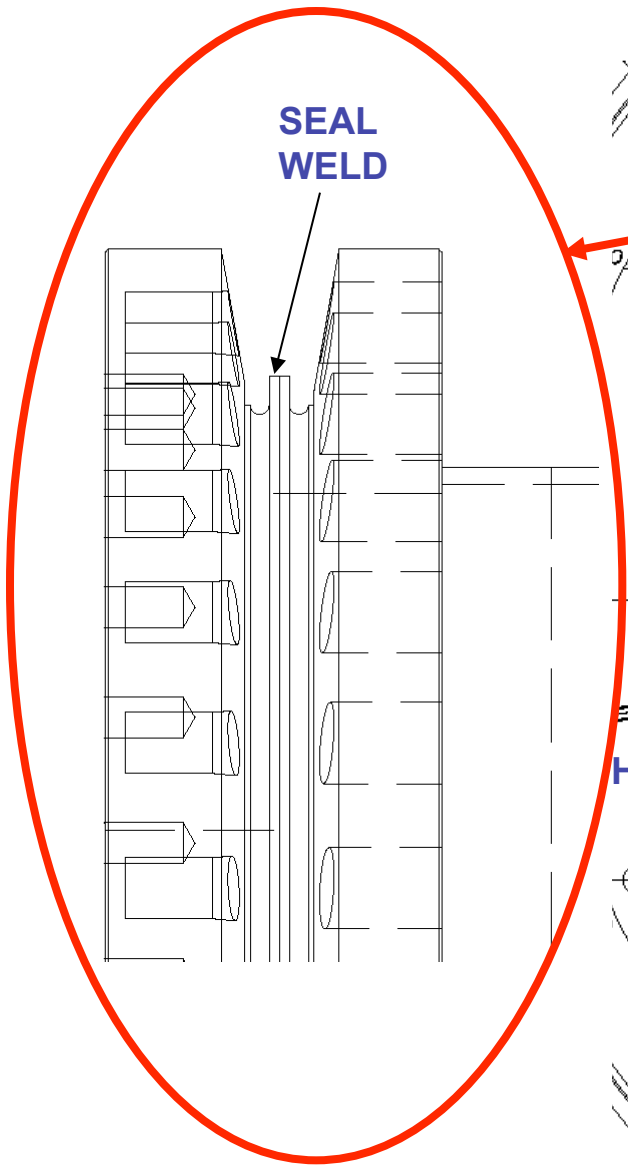




D2O Purity 2006-2008

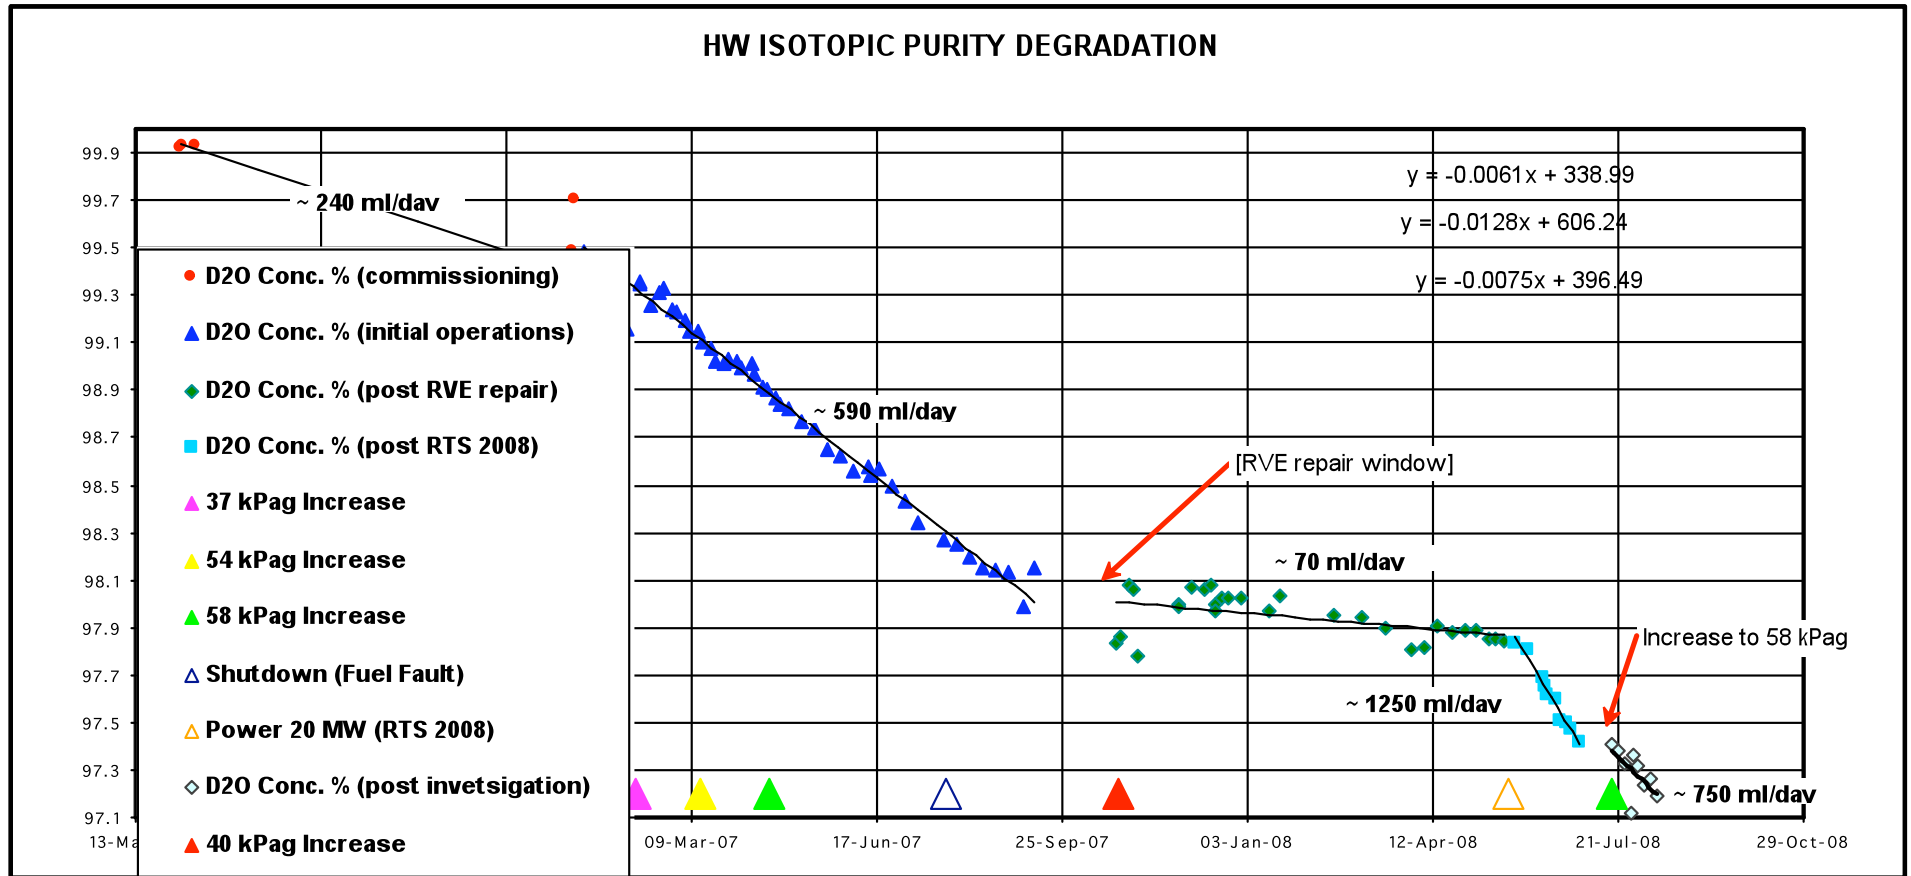


Nucleonic channels data - 2007



Nucleonics drift (normalised to thermal balance)

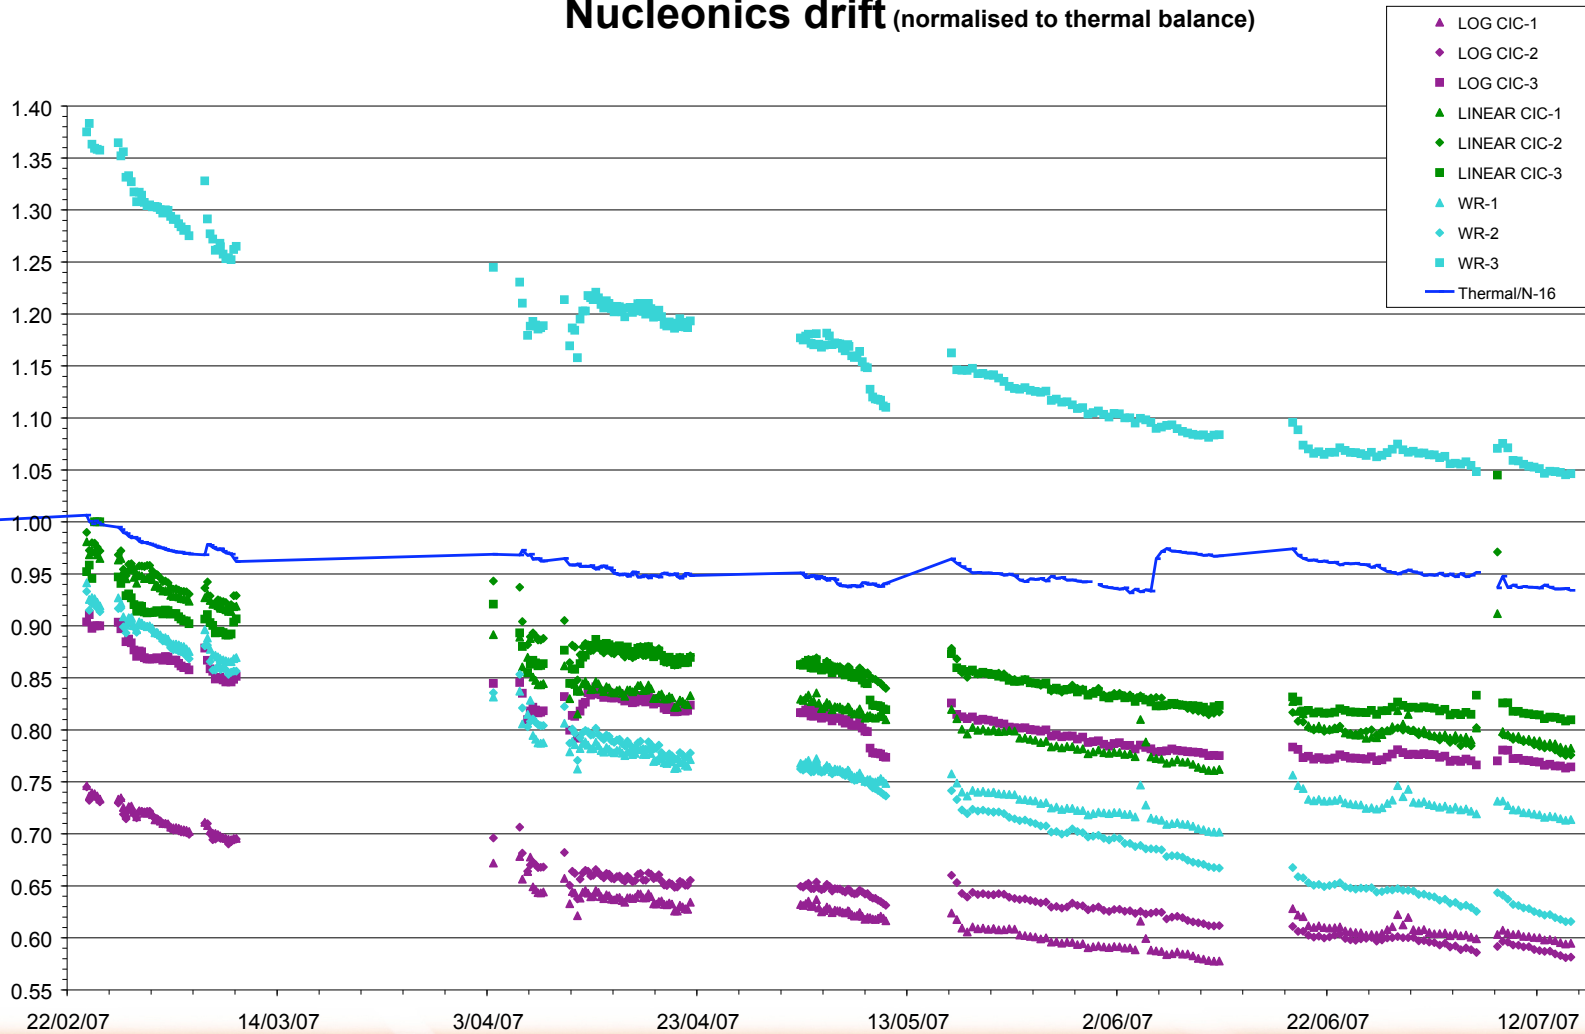

Nucleonic channels data - 2008

Nucleonics constants

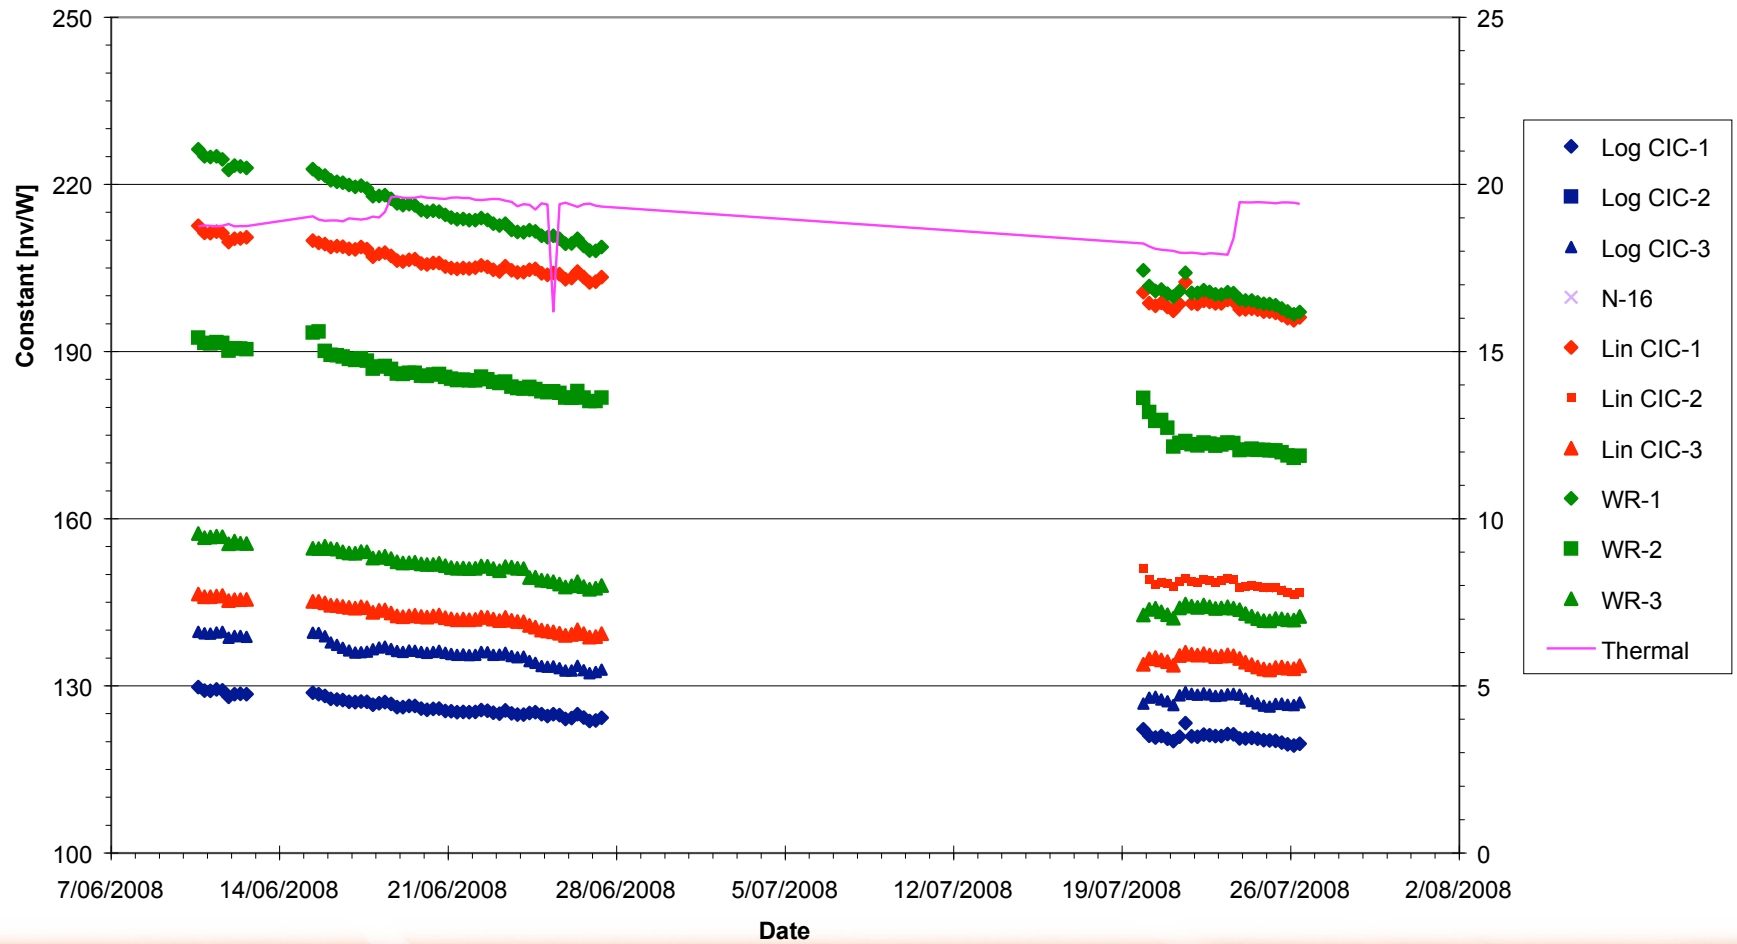

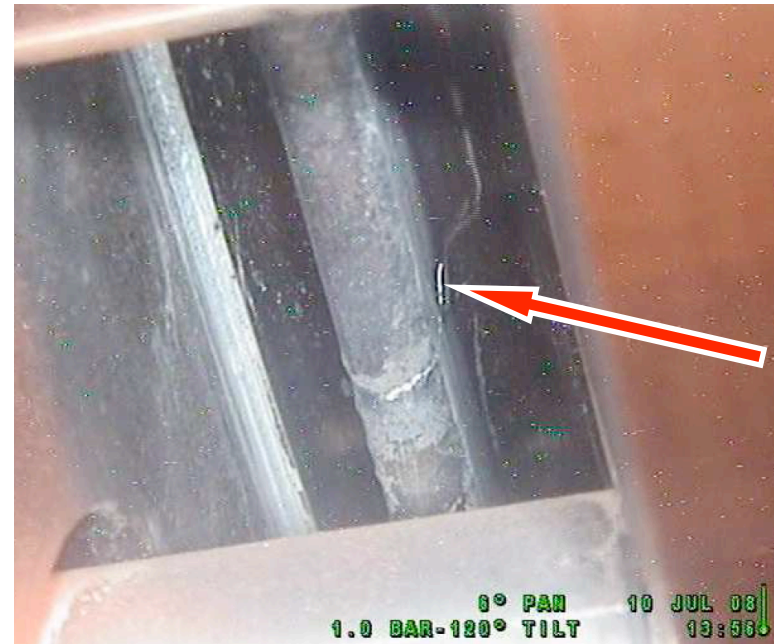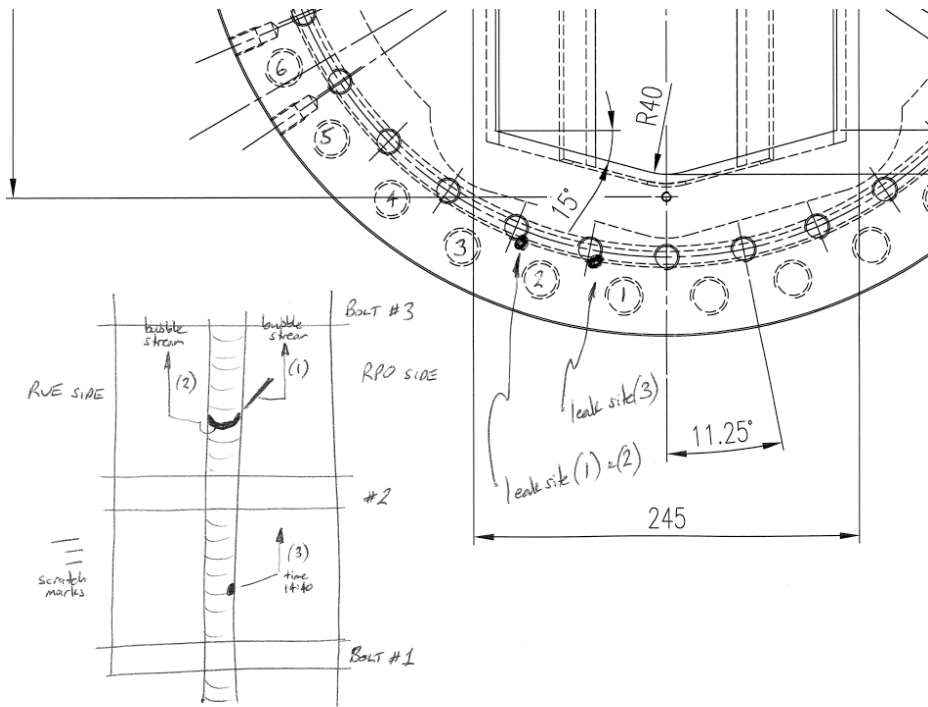

Analysis

- No new leak sites identified
- Estimated leak site diameter ~20 micron.
- Estimated leak site length of 20-200 micron.
- Temperature effect may be due to variation in water viscosity
- Alumina injection now largely ineffective


Requirements

- Understand the defects on RVE
- Protect integrity of RVE
- Optimise reactor operation time and performance
- Minimise leak-rate prior to HWU plant installation
- Monitoring of D20 purity
- Control leak-rate

Options for mitigation of leaks


- Heavy water replacement
 - Allows operation to continue and major projects to progress
- Global pressure control
 - Increase cover gas pressure
 - Safety submission likely – increased risk of tritium in RPO
- Local pressure control
 - Flow loop around beam flanges
 - Mock up tested – may require ARPANSA approval
 - Ready in ~1 month
- Leak-site clamp (leak-site “epoxy”)
 - Local and no moving parts
 - Ready in 1-2 months
- Temperature adjustment
 - Requires safety analysis and submission
- Particle re-injection
 - Not favoured

Mock-ups

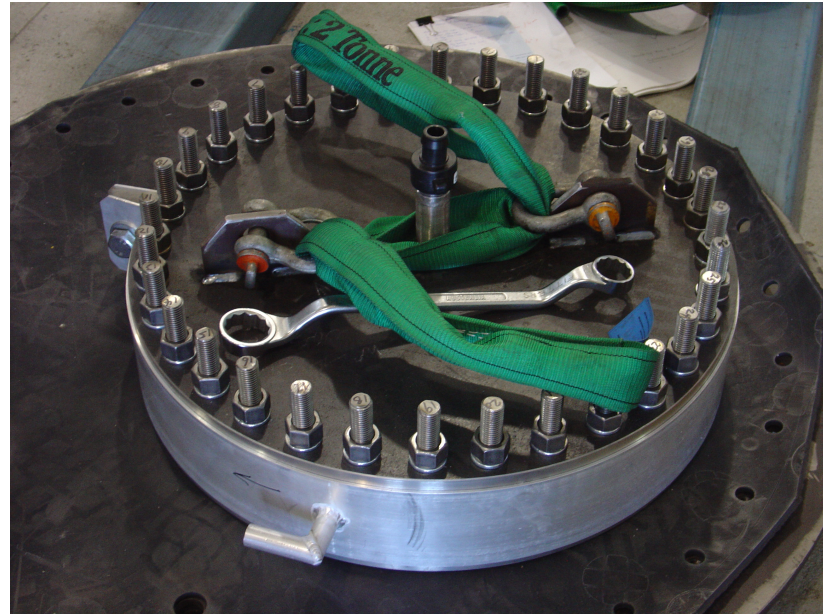

Heavy Water Enrichment


- Distillation is feasible
- Mature technology
- A significant height of distillation column is necessary (20 to 30 m)
- Not energy efficient
- Long lead time
- Reactor down time

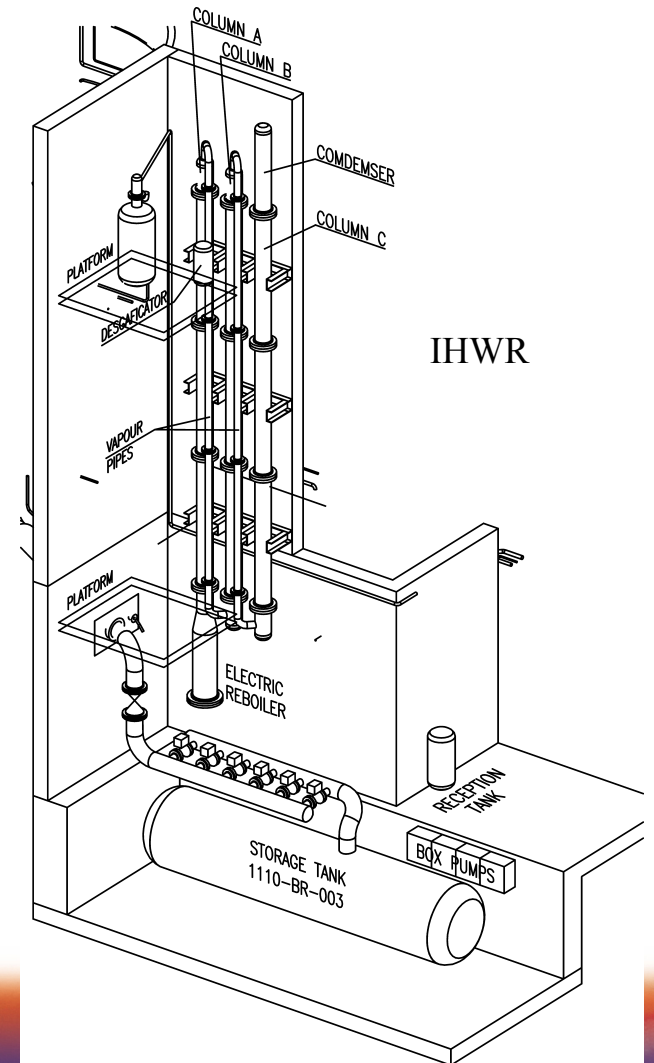

HW Isotopic Purification


- HW isotopic purification plant designed
- Detailed engineering design review undertaken
- Preferred option is a separate building for the distillation columns will permanent connection to the reactor heavy water system
- Safety submission prepared, submitted and approved to construct and “cold commission”
- Plant construction is being completed now

Still Operating

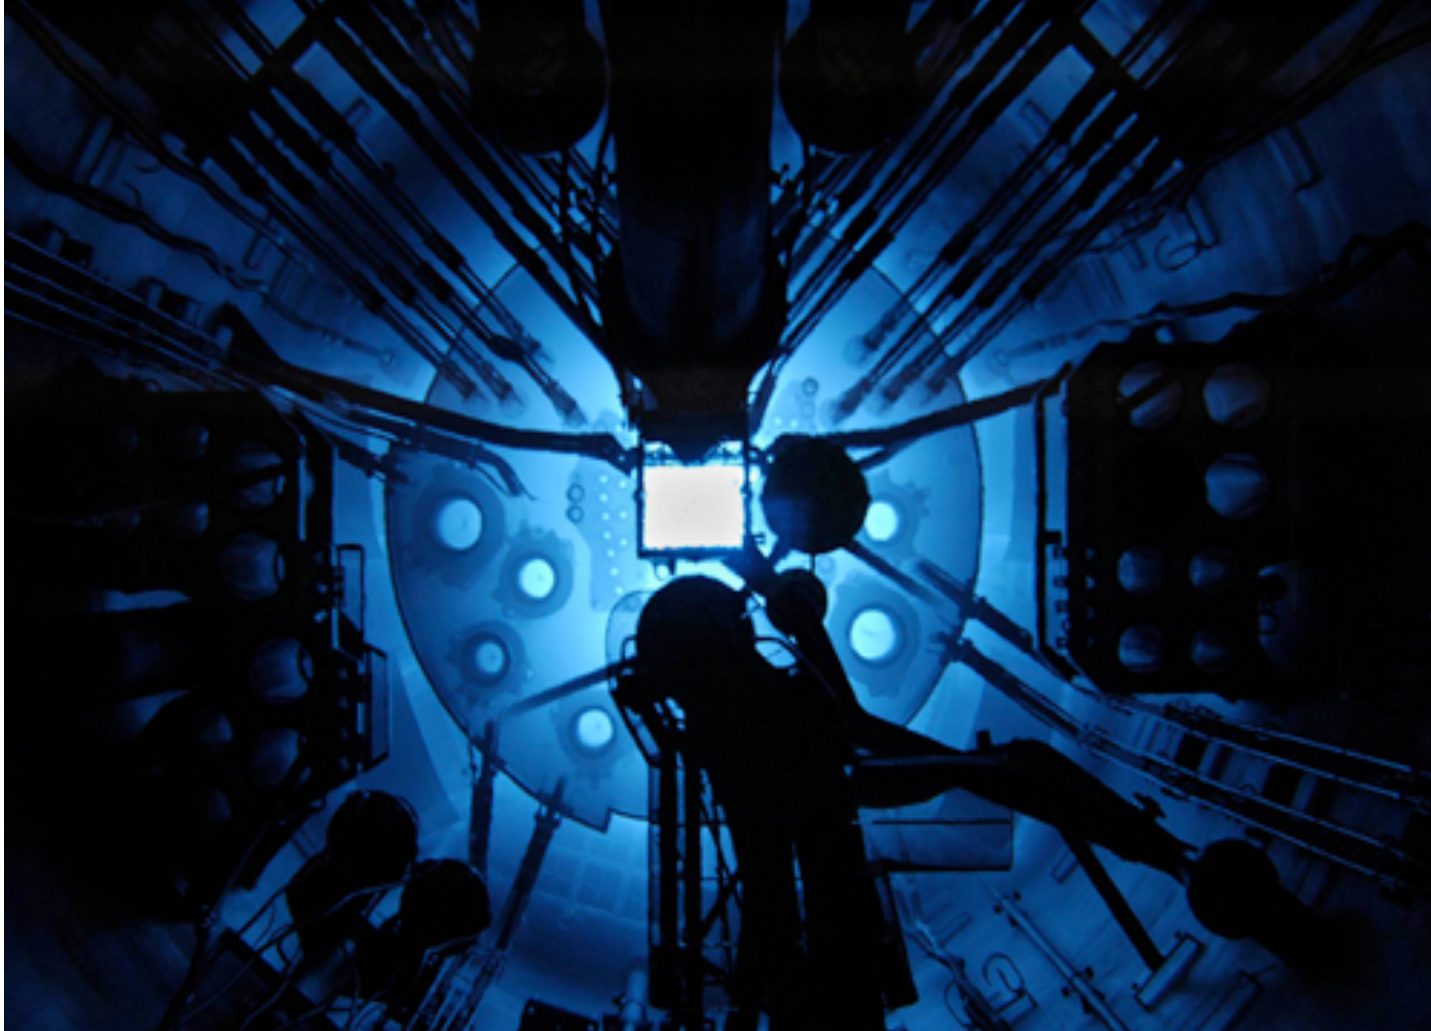

10/4/10
Australian Government

Ansto


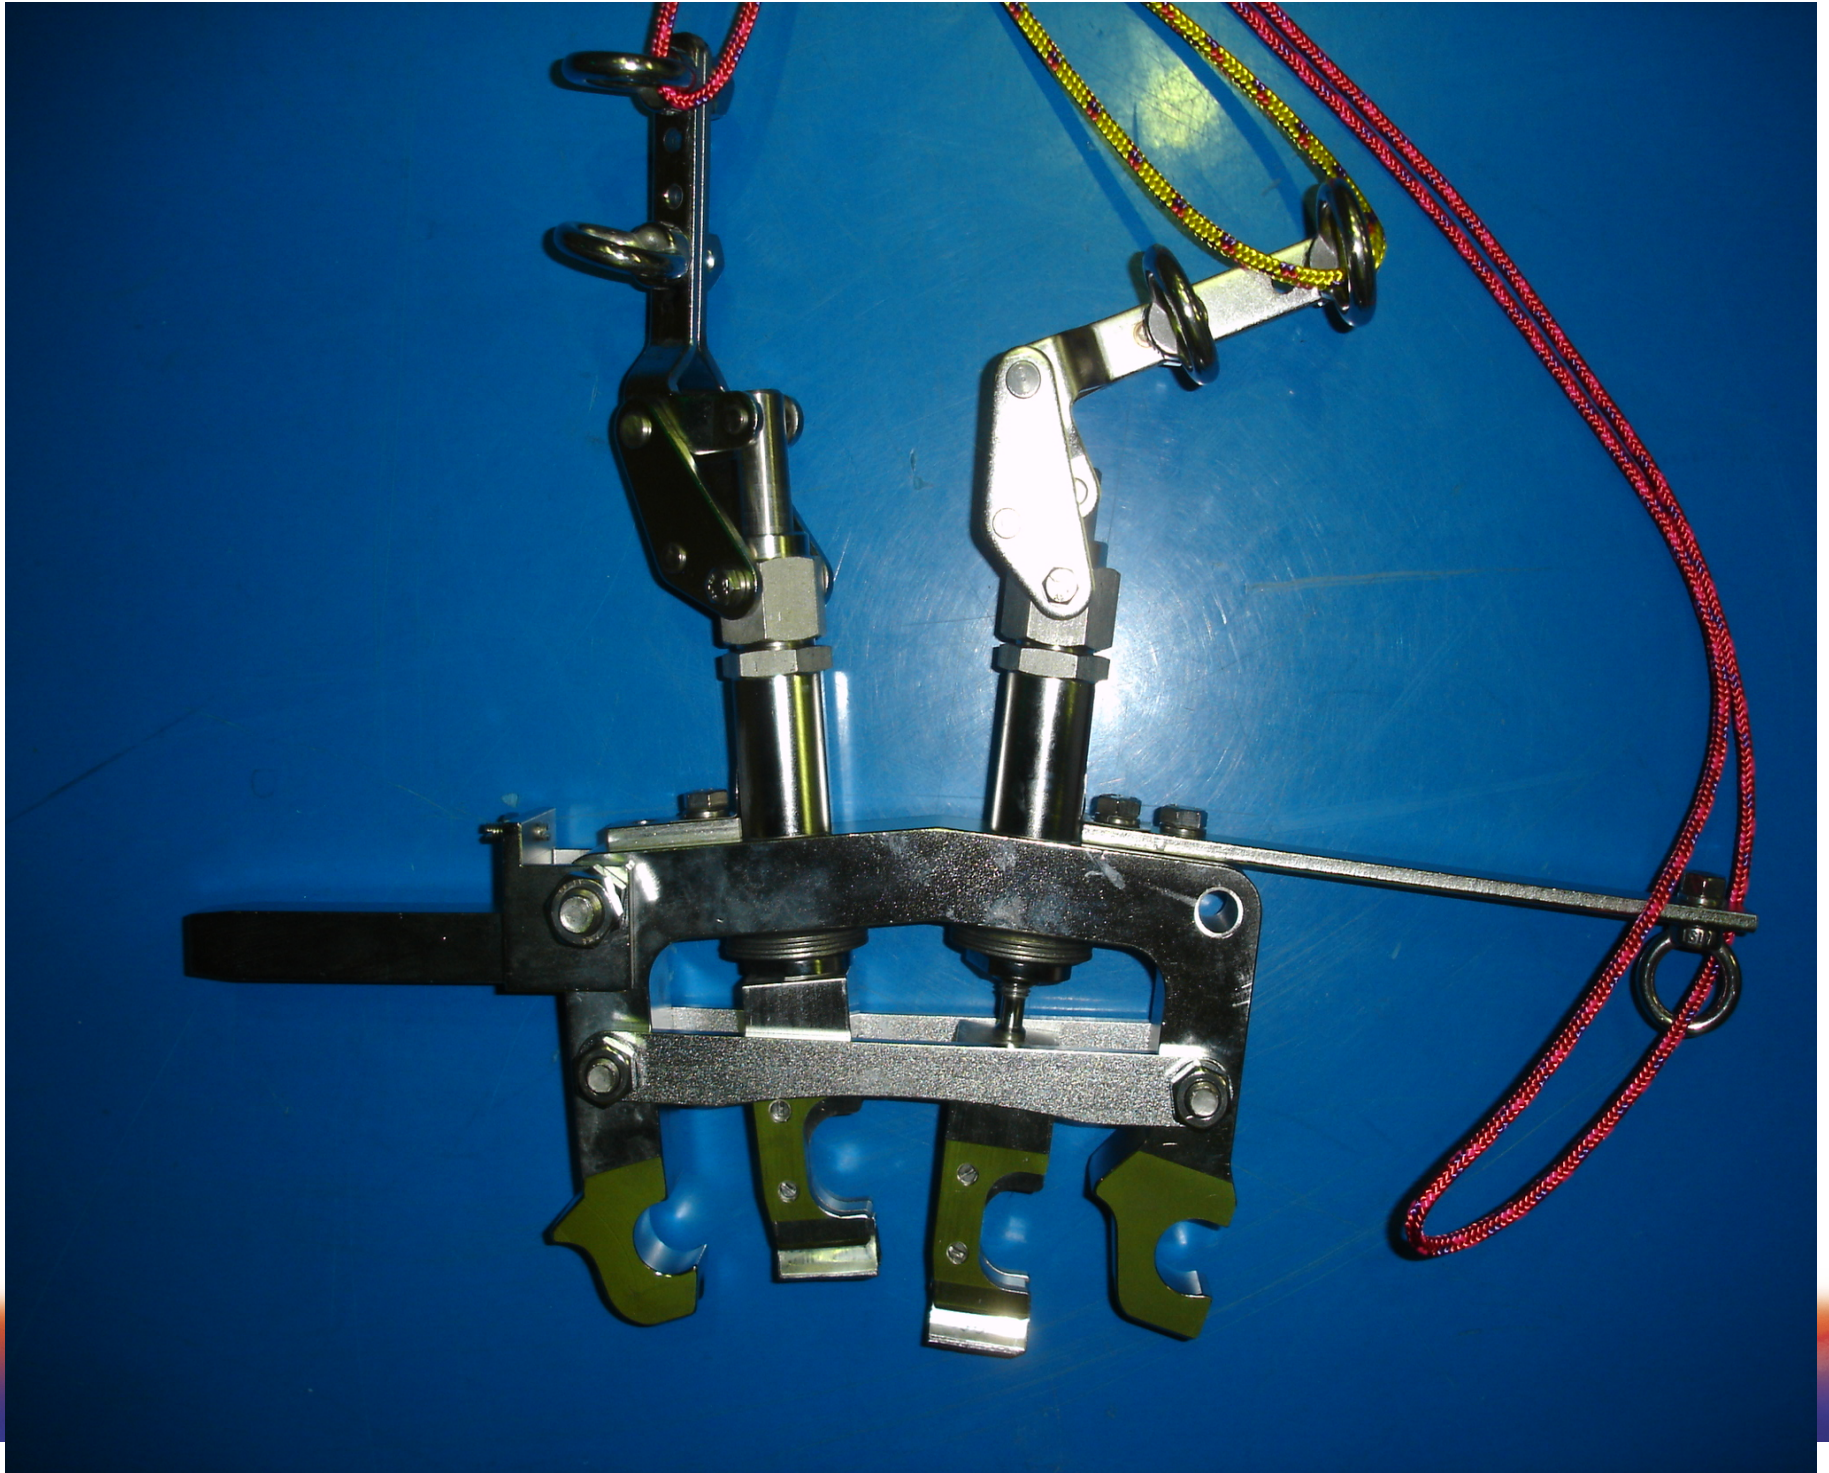



Reflector Vessel Trial Repair

Application of Clamps


Nov – Dec 2009

- Remove fuel
- Lower Reactor Pool water
- Drain RVE
- Over-pressurise – He bubbles
- Apply clamps – graphite pads
- Bubbles halted on major leak sites
- Return to service
- Measured D2O purity

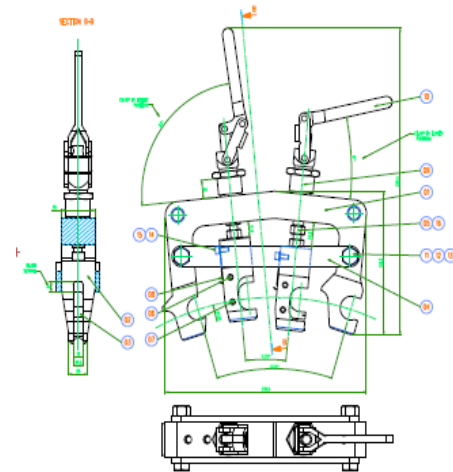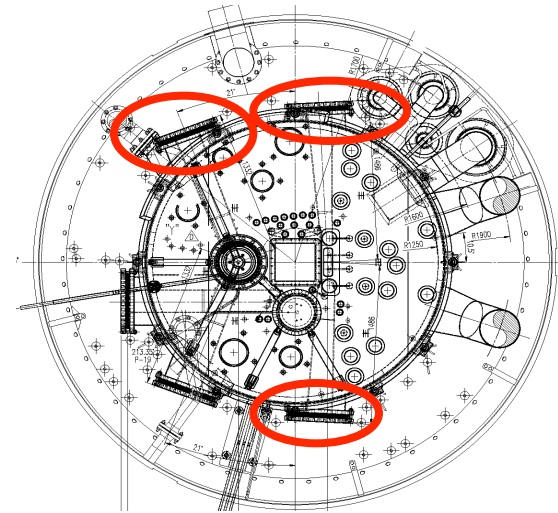


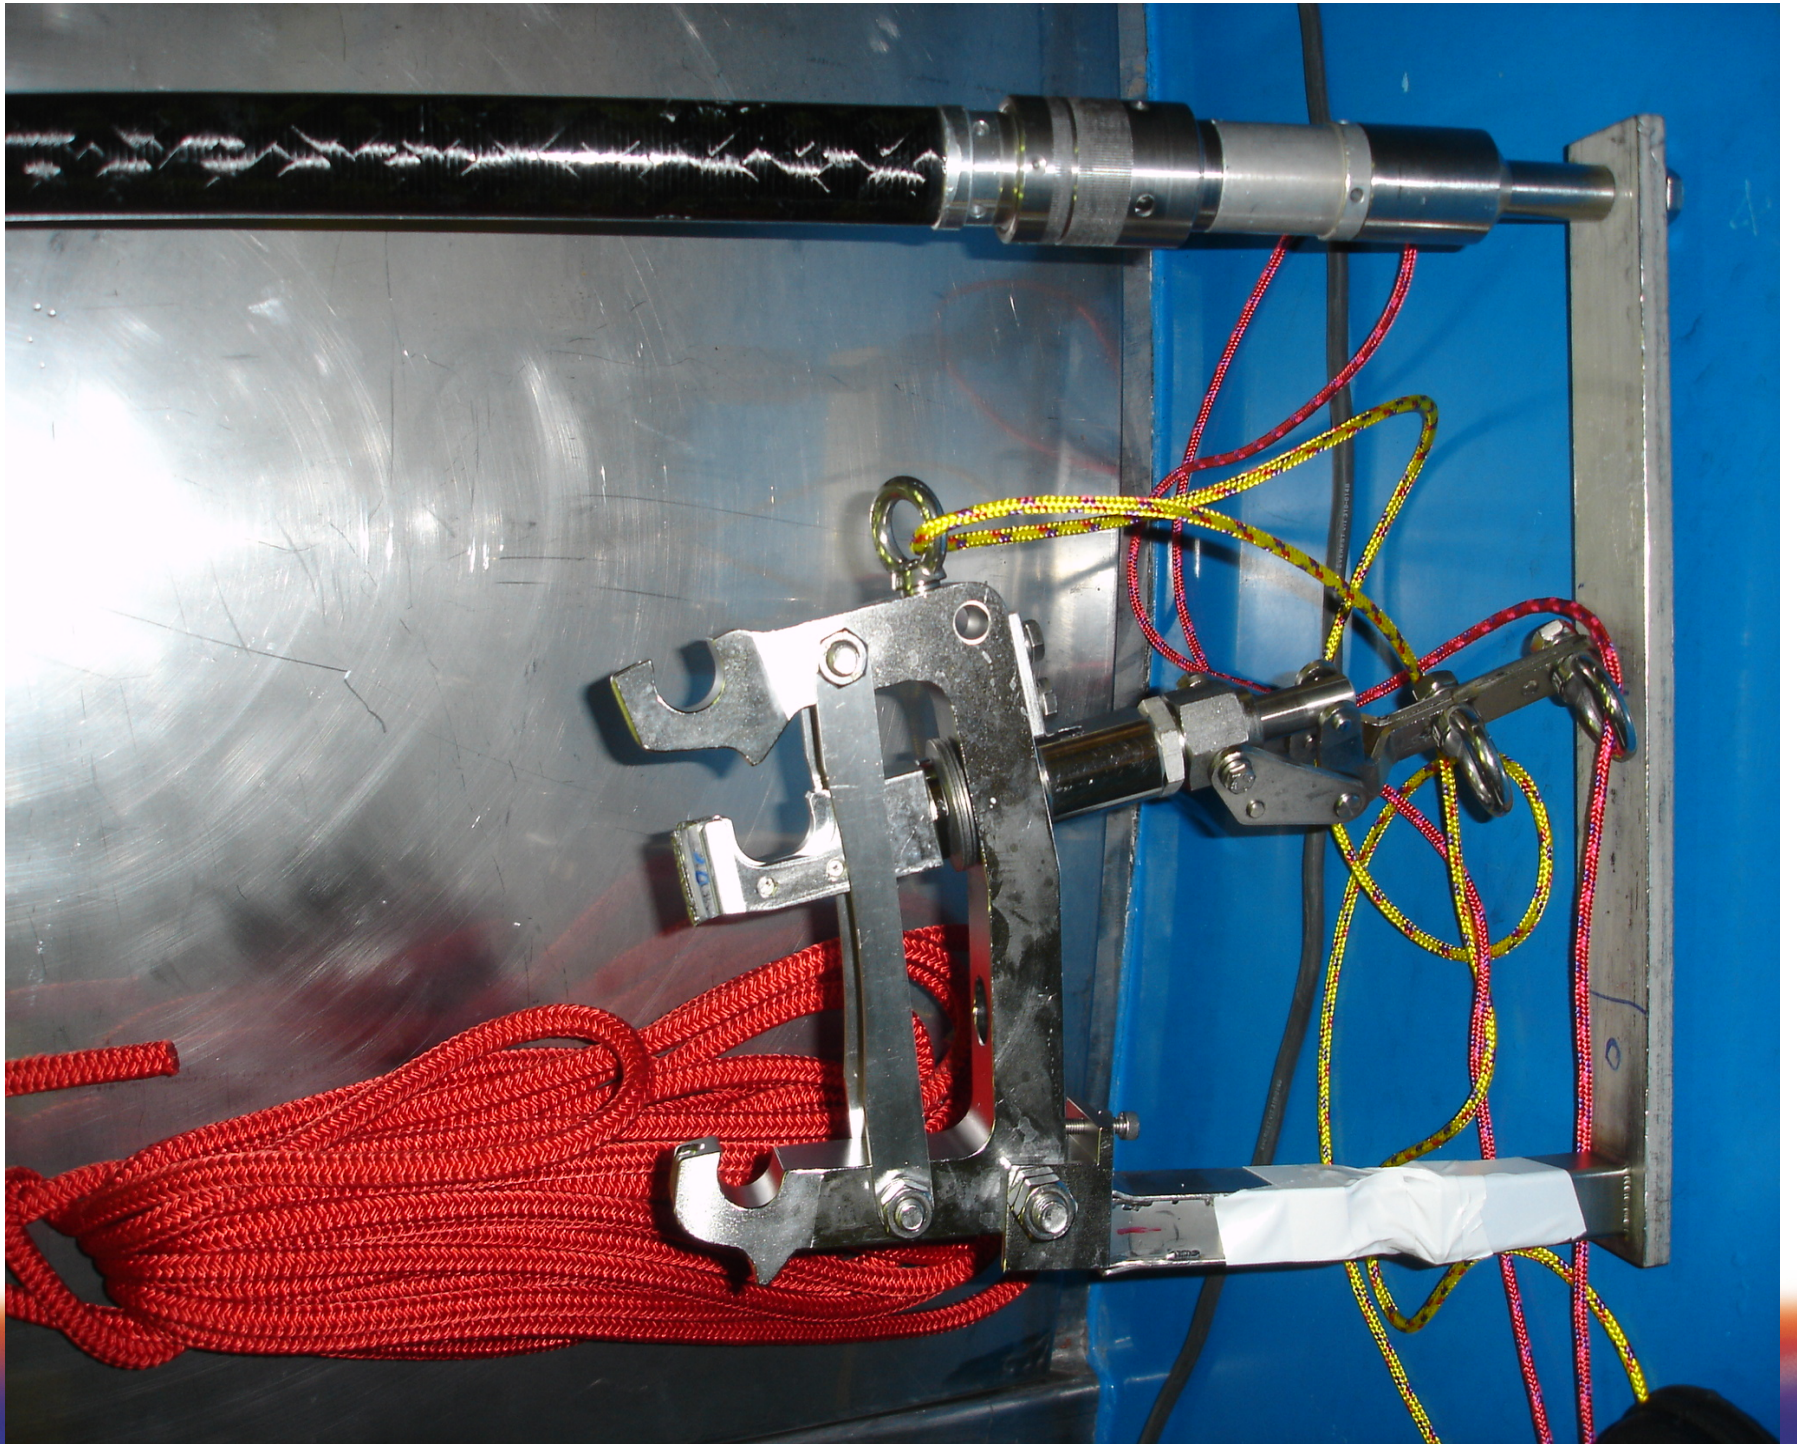



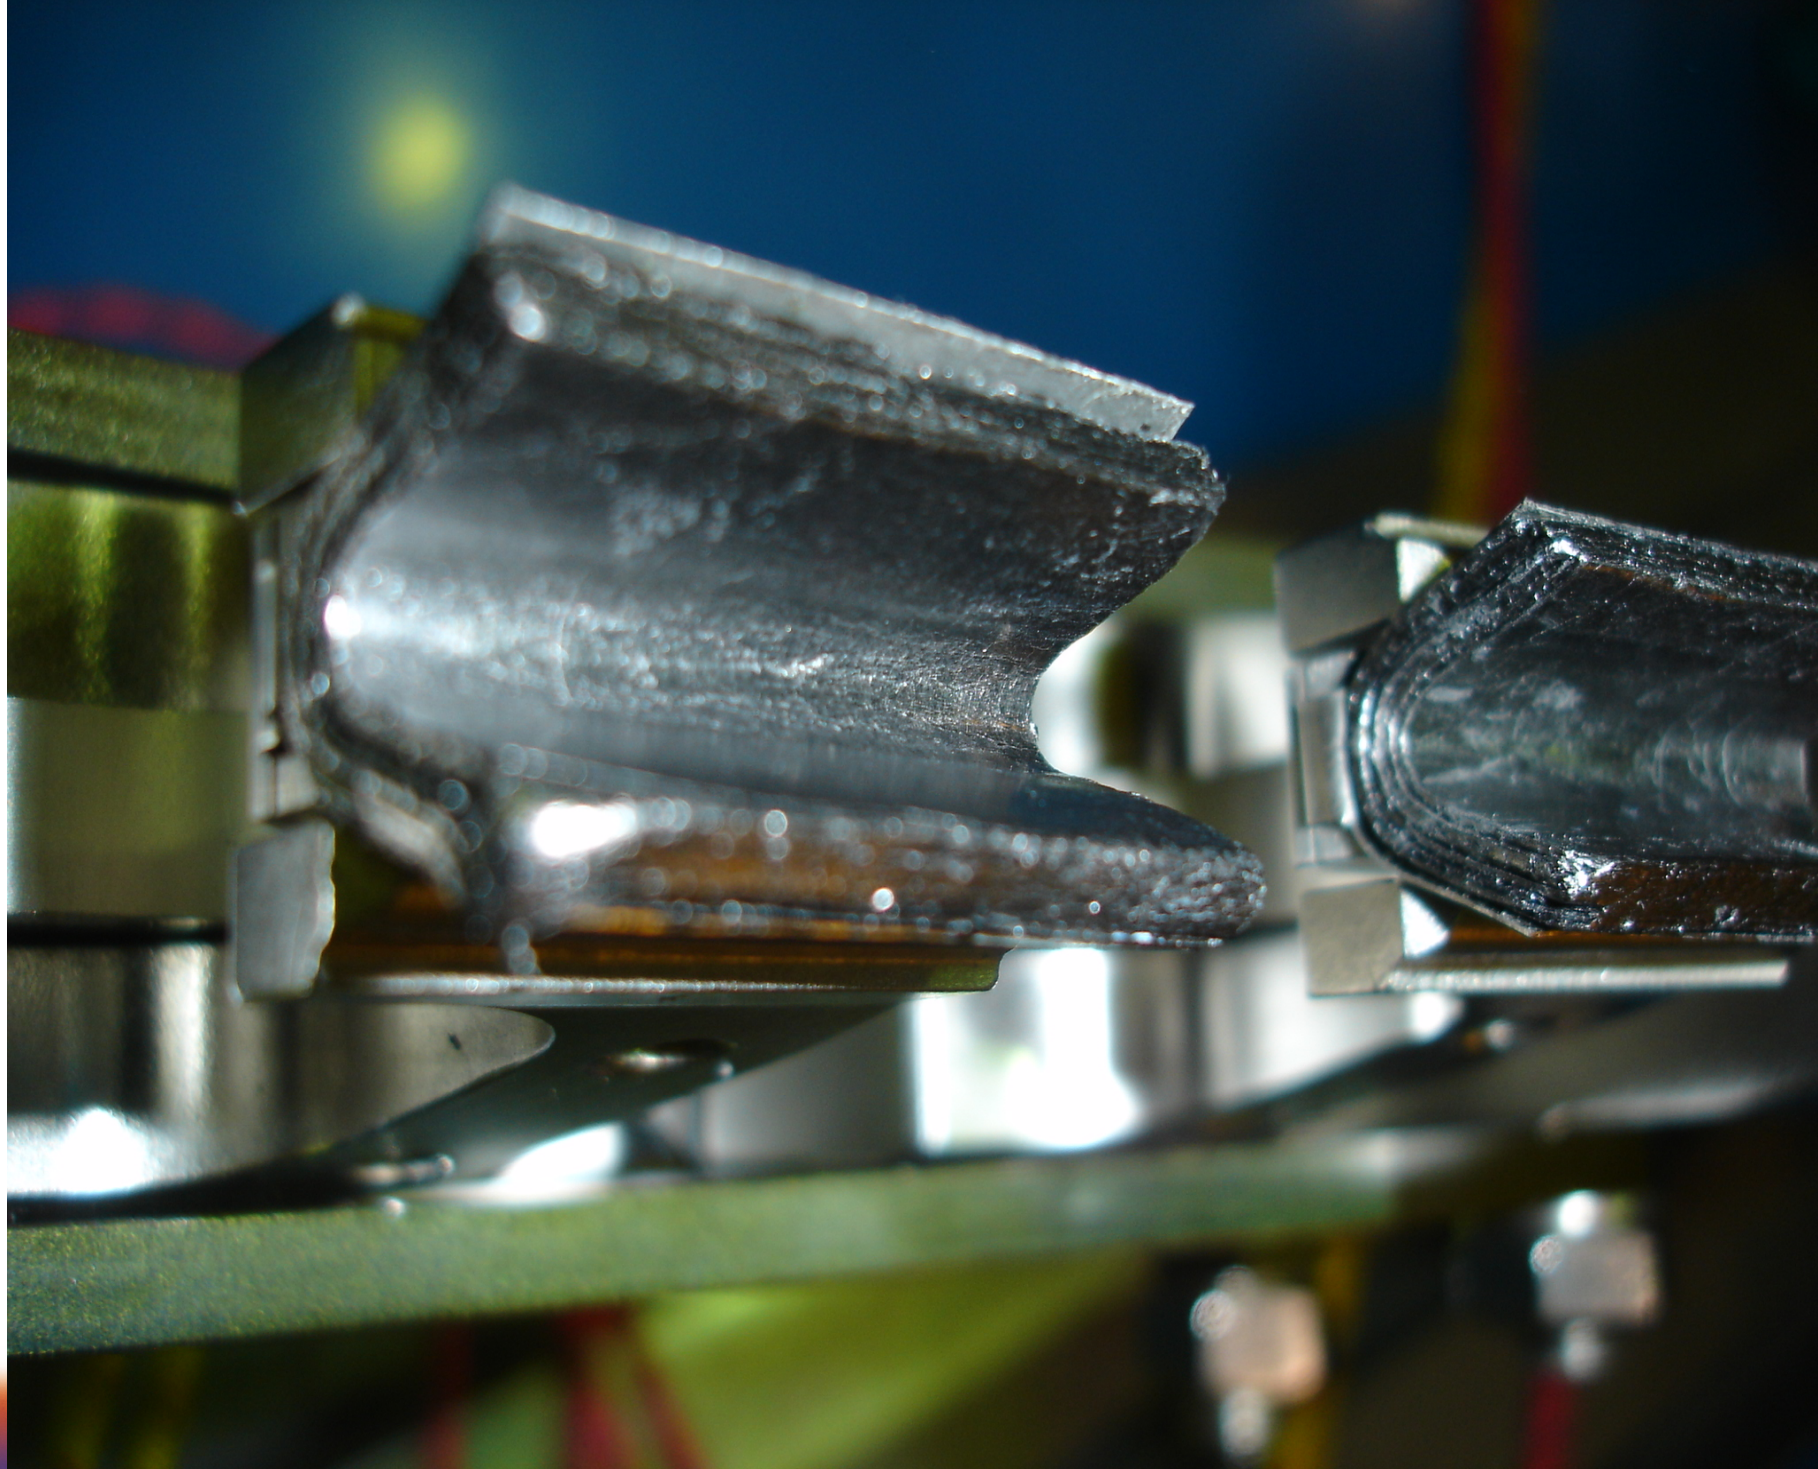

Latest Heavy Water Purity Data

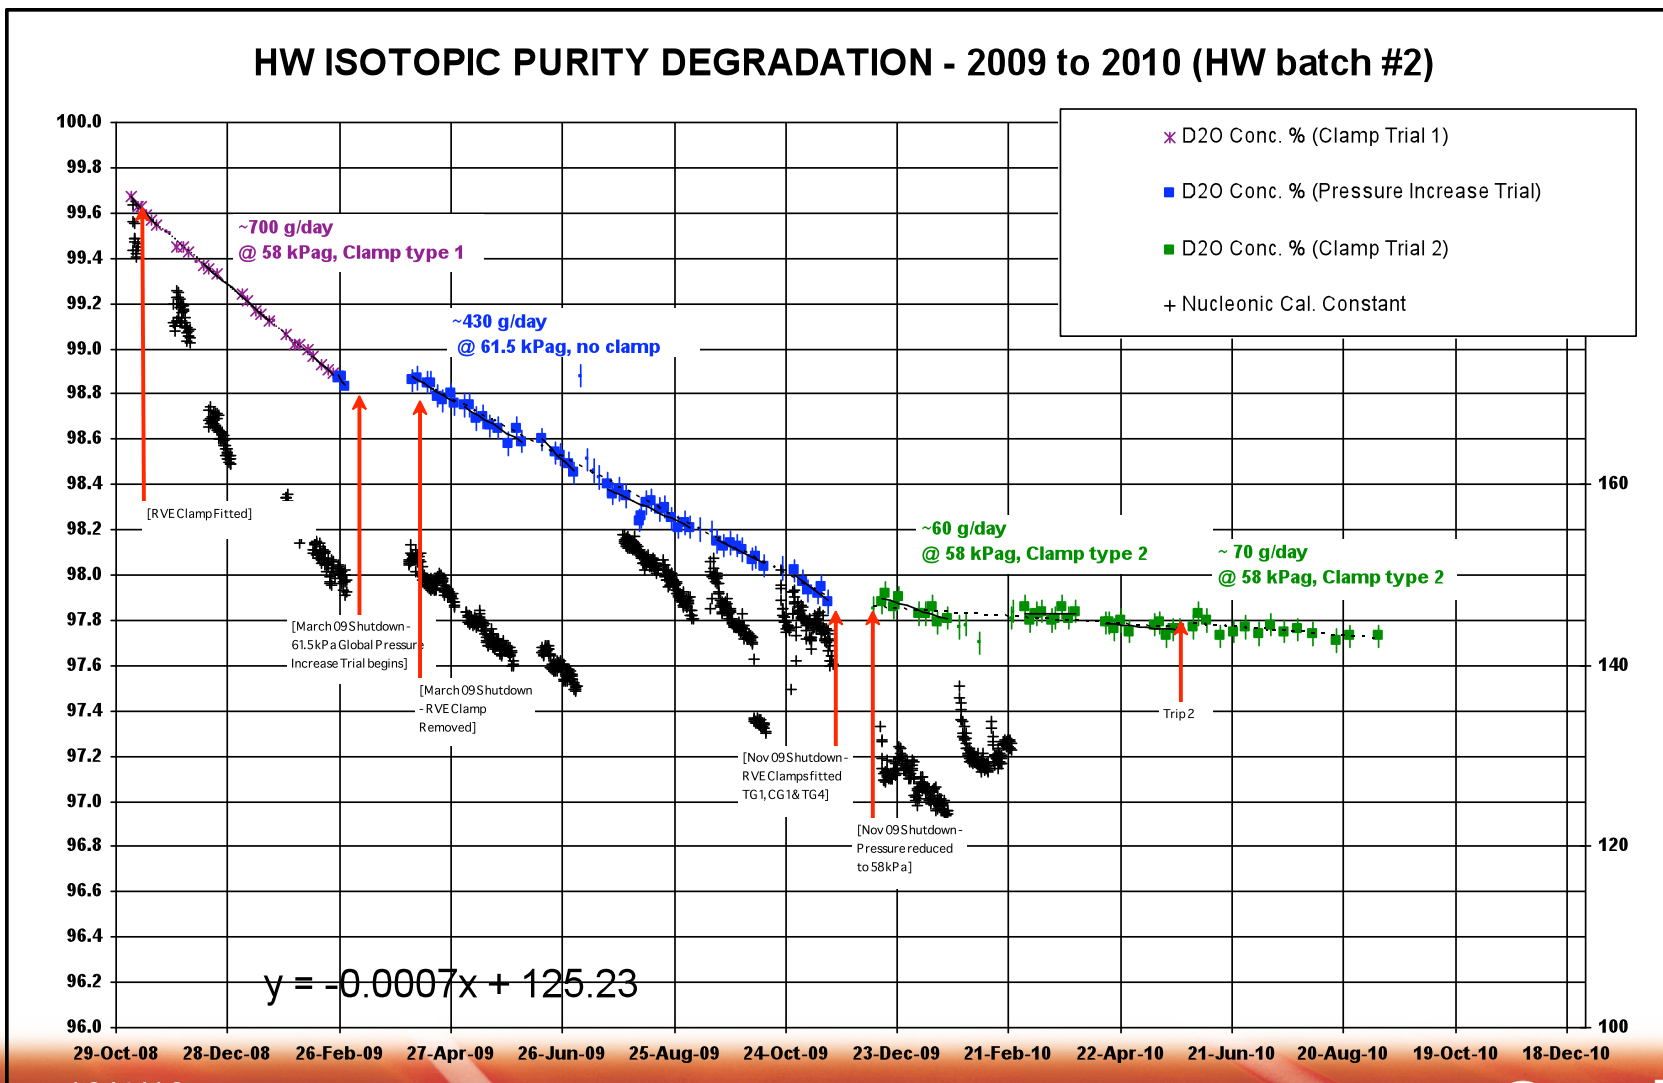

10/4/10

Australian Government



Current & next steps

- **Maintain clamps in position**
- **Manufacturing spares**
- **Visual monitoring**
- **Measuring D2O purity – once per week**
- **Monitoring nucleonics channel responses**
- **Keep extant other engineering projects with long-term promise**
- **Heavy Water Isotopic Purification System constructed and commissioned in 2011**


Root Cause

- Defects caused by delayed hydride cracking
- Stress analysis has shown that there is no significant residual stresses in the weld

A group of six people, three men and three women, are standing on a yellow metal platform. They are all wearing bright yellow lab coats and blue gloves. They are leaning on a stainless steel railing. The platform is part of a larger industrial structure. In the background, there are various pieces of equipment, including a control panel with a digital display showing '068.17540'. The setting appears to be a laboratory or a specialized industrial facility.

OPERATIONS BRIDGE 244/80

Still Operating

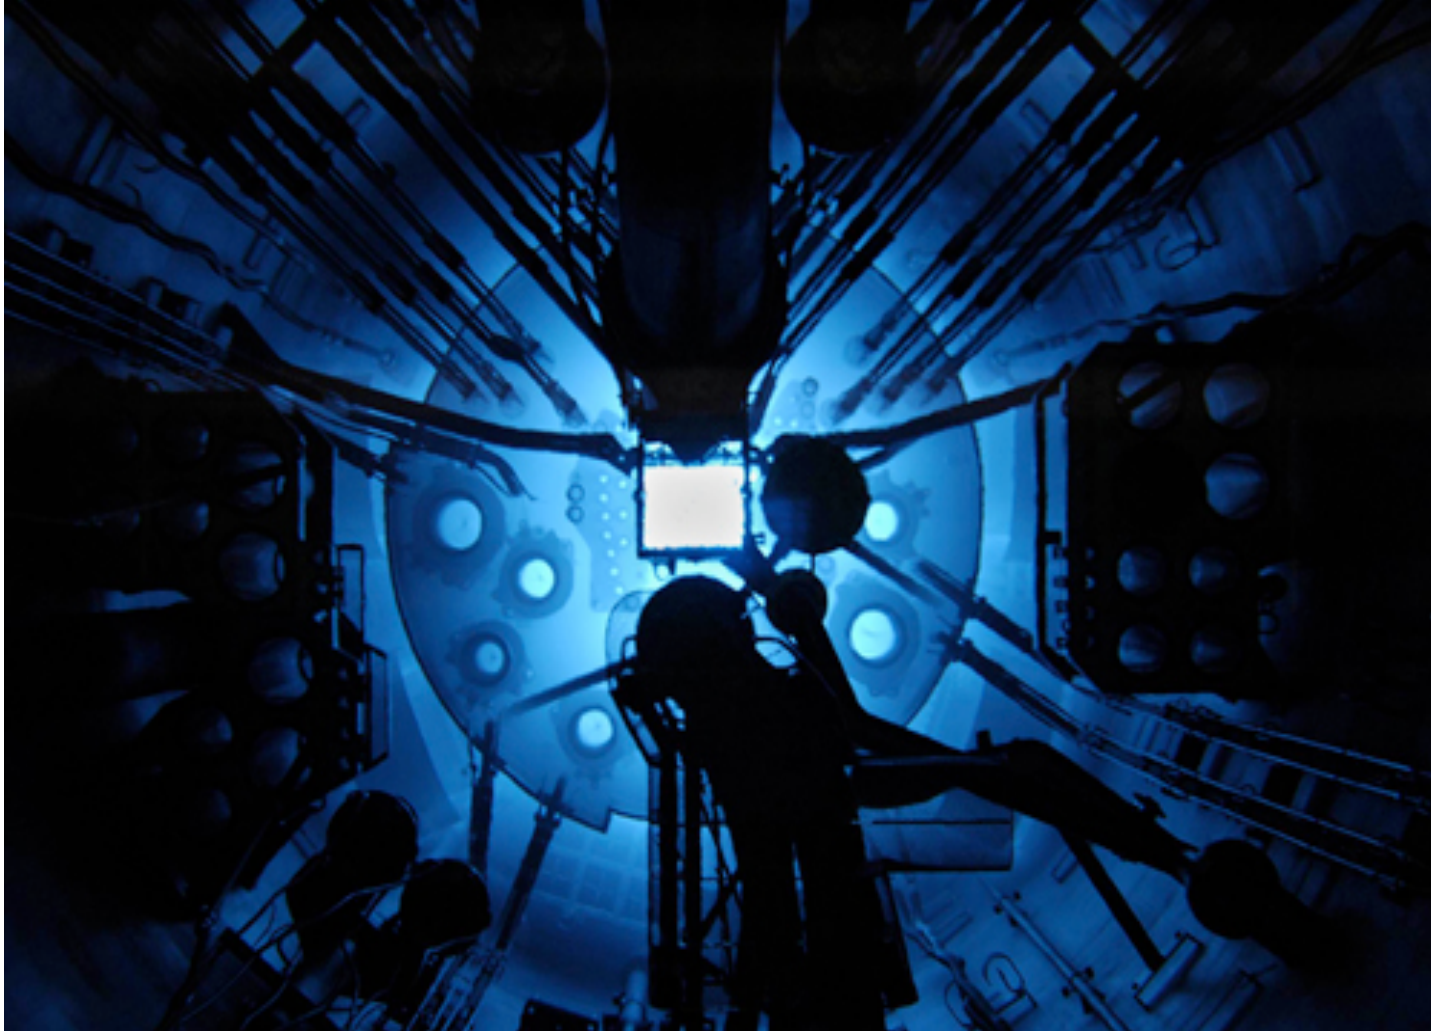

10/4/10
Australian Government

Ansto

The ANSTO logo features a stylized white 'a' inside a circle, followed by the letters 'nsto' in a bold, sans-serif font. The background is a vibrant blue with dynamic, glowing light streaks that create a sense of motion and energy.

ansto

Nuclear-based science benefiting all Australians